

A GUIDE TO  
PHOTOGRAPHY,

CONTAINING

A CONCISE HISTORY OF THE SCIENCE AND ITS CONNECTION WITH  
OPTICS, TOGETHER WITH SIMPLE AND PRACTICAL  
DETAILS FOR THE PRODUCTION OF PICTURES BY THE

CHEMICAL ACTION OF LIGHT

UPON PREPARED SURFACES OF

PAPER, GLASS, AND SILVERED PLATES,

INCLUDING

PHOTOGENIC DRAWING,

TALBOTYPE OR CALOTYPE, DAGUERRETYPE,

AND THE IMPROVED PROCESSES FOR OBTAINING

VIEWS, PORTRAITS, ETC. ;

WITH PREPARED

COLLODION AND ALBUMEN.

---

BY W. H. THORNTHWAITE,

*Author of "Photogenic Manipulation," &c.*

---


ILLUSTRATED WITH WOODCUTS.

THIRD EDITION.

London :

HORNE, THORNTHWAITE, & WOOD,  
OPTICIANS AND PHILOSOPHICAL INSTRUMENT MAKERS,  
121 and 123, NEWGATE STREET.

1851.

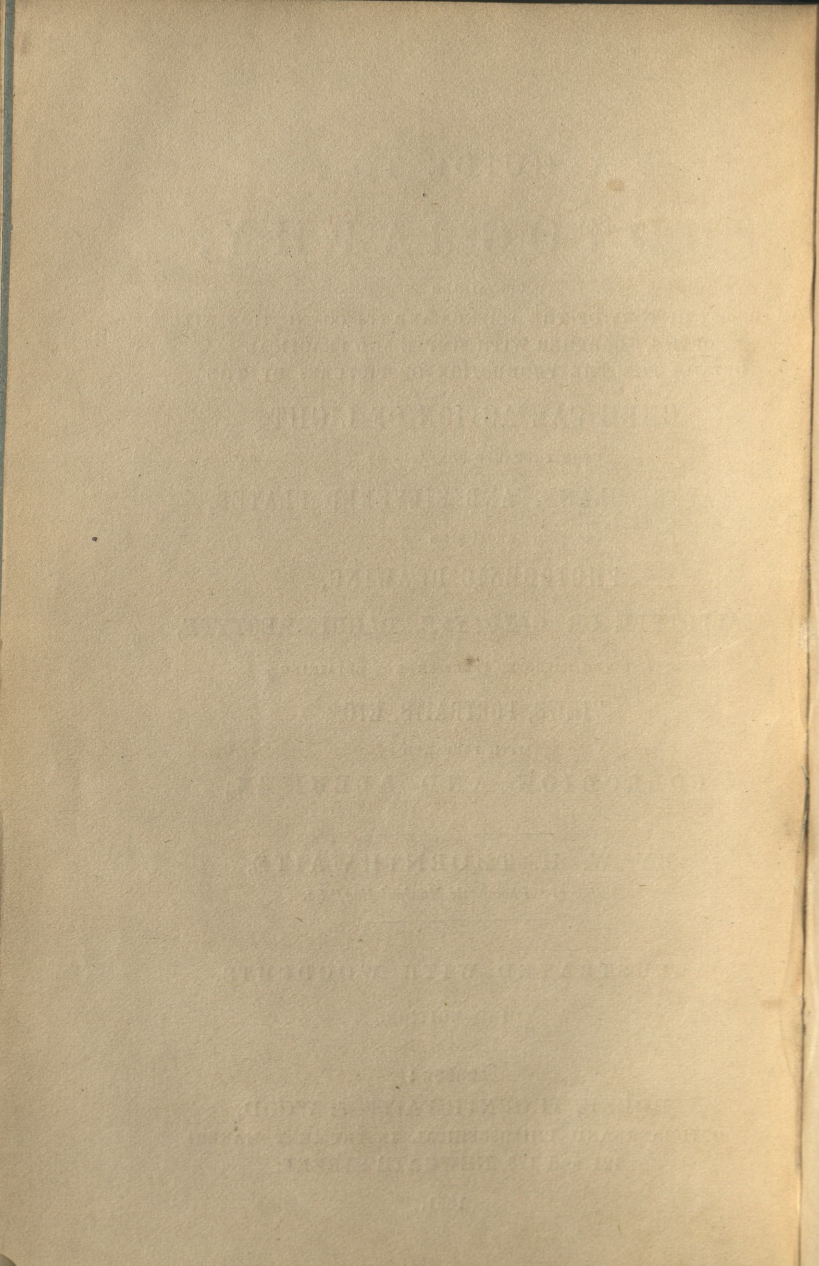

9  
79

# A GUIDE TO PHOTOGRAPHY,

CONTAINING  
A CONCISE HISTORY OF THE SCIENCE AND ITS CONNECTION WITH  
OPTICS, TOGETHER WITH SIMPLE AND PRACTICAL  
DETAILS FOR THE PRODUCTION OF PICTURES BY THE

CHEMICAL ACTION OF LIGHT

UPON PREPARED SURFACES OF  
PAPER, GLASS, AND SILVERED PLATES,

INCLUDING  
PHOTOGENIC DRAWING,  
TALBOTYPE OR CALOTYPE, DAGUERRETYPE,

AND THE IMPROVED PROCESSES FOR OBTAINING

VIEWS, PORTRAITS, ETC. ;

WITH PREPARED  
COLLODION AND ALBUMEN.

---

BY W. H. THORNTHWAITE,

*Author of "Photogenic Manipulation," &c.*

---

ILLUSTRATED WITH WOODCUTS.

THIRD EDITION.

London :

HORNE, THORNTHWAITE, & WOOD,  
OPTICIANS AND PHILOSOPHICAL INSTRUMENT MAKERS,  
121 and 123, NEWGATE STREET.

1851.

A GUIDE TO  
PHOTOGRAPHY,

A CONCISE HISTORY OF THE SCIENCE AND ITS CONNECTION WITH  
OTHER BRANCHES OF KNOWLEDGE WITH SIMPLE AND PRACTICAL  
DETAILS FOR THE PRODUCTION OF PICTURES BY THE

CHEMICAL ACTION OF LIGHT

AND THE

PAPER, GLASS, AND OTHER PLATES

BY

PHOTODUPLICATION

TALBOTYPE OR CALOTYPE, PAPER, GLASS, AND OTHER PLATES

AND THE

VIEWS, PORTRAITS, ETC.

WITH

QUESTIONS AND ANSWERS

BY W. B. THORNTON

Author of "Photography and its Applications," &c.

ILLUSTRATED WITH WOODCUTS

THIRD EDITION

LONDON:

HORN & THORNTON

OPTICIAN AND PHOTOGRAPHICAL INSTRUMENT MAKER

121 AND 123, THE STRAIT

LONDON: PALMER and CLAYTON, Printers,  
Crane-court, Fleet-street.

## P R E F A C E.

---

As most of the publications on Photography, both here and on the Continent, contain so many new processes and modifications, which, although extremely interesting as connected with the art, are comparatively useless except to the advanced Photographer, I have thought that a "Guide" was still required for those who, knowing but little of the subject, might desire to commence this useful and interesting pursuit; and which should only contain that method of proceeding, in each specific process, which has been found most uniformly to produce the best results with the least amount of trouble. The following pages, I trust, will supply this desideratum, and in this hope are submitted to the public.

W. H. T.

123, NEWGATE STREET,

*December, 1851.*

# CONTENTS.

---

	PAGE
INTRODUCTION .....	1
Photographic apparatus .....	16
Cameras .....	18
Camera-stands .....	24
Filtration .....	25
Distillation .....	26
Photographic chemicals .....	27
Photogenic drawing .....	30
Selection of paper for ditto .....	32
Preparation of paper for ditto .....	33
Fixing the photogenic drawing .....	37
Negative and positive photographs .....	38
Calotype, or Talbotype .....	39
Iodizing the paper .....	40
Preparing the paper for camera .....	43
Exposure in the camera .....	44
Bringing out the picture .....	44
Fixing the picture .....	45
The printing process .....	46
Daguerreotype .....	47
Cleaning the silvered plate .....	49
Applying the sensitive coating .....	53
Exposure in the camera .....	56
Mercurialising the plate .....	57
Removing the sensitive coating .....	58
Fixing the picture .....	58
Colouring daguerreotypes .....	59
Electro-silvering daguerreotype plates .....	60
Photography on glass .....	61
Collodion pictures .....	61
Preparation of collodion .....	64
Albuminized glass plates .....	64
Portraits, views, &c. ....	66
Preparation of albuminized paper .....	68
Fixing the positive proof .....	69
Photographs on wax paper .....	71
Mr. Fox Talbot's instantaneous process .....	72

ON  
PHOTOGRAPHY & DAGUERRETYPE.

By W. H. THORNTHWAITTE,  
AUTHOR OF "PHOTOGRAPHIC MANIPULATION,"  
&c., &c., &c.

INTRODUCTORY REMARKS.

THE art of making sun pictures, whether on paper or films of various kinds, or silver plates—may be designated under the general term photography—a term derived, as is well known, from the two Greek words *phōs*, light, and *graphō*, I write or delineate, and includes various specific operations to which the appellations Calotype, Talbotype, Daguerreotype, and Photography, have at different periods, and on various occasions, been given. All these operations will be treated of in detail; such as concern the depiction of forms on paper and tissues first coming under consideration, and on metals afterwards. But, as a preliminary to both, it will be necessary that we should acquire a true idea of the nature and properties of light.

Of the ultimate constitution of light we positively know no more at the present day, than did Plato, Pythagoras, or Aristotle; but the assiduous efforts of philosophers, since the prosecution of inductive philosophy, have made us well acquainted with many of its physical and chemical qualities.

Two leading theories, more or less developed, have existed since the days of Pythagoras—at least in relation to the nature of light. According to the one theory, it was assumed to be composed of wavy oscillations in some ill-understood medium, which was supposed to fill all space; according to the other, it was a congeries of actual physical emanations from luminous bodies—emanations which were assumed to be so far material that hopes were entertained of the possibility of weighing them, by balances of an exceedingly delicate make. The first is called the undulatory, the second the corpuscular, theory of light. Now, the undulatory theory of light

although adopted by many of the ancients, only assumed consistent shape in the days of Huyghens, who was born a few years before Newton, and, so far as England is concerned, is a theory of very modern adoption; for Newton was violently opposed to the undulatory or wave theory of light, and the prestige of his great name caused it to remain in abeyance until the early part of the present century, when the discovery of polarized light, and the investigation of the laws of double refraction, made known many phenomena which were totally irreconcilable with the Newtonian theory, although easily explicable by the theory of undulation. Hence the latter gained new force, and at the present day may be said to be universally adopted.

We need not carry this description further; for all our future purposes—the operation of light not its ultimate nature—will alone have to be treated of. Now, the operation of light is either optical or chemical. As an optical agent, its properties all depend on the property it has of acting in straight lines, thus giving rise to the idea of a ray; as a chemical agent, our knowledge is bounded by the mere cognisance and expression of certain facts, concerning the ultimate rationale of which we are completely in the dark.

As I shall presently have to treat of rays of light, it is necessary at once to say that the term is merely conventional. If light be composed of undulations or waves, as we assume to be the case, then it is clear there can really be no such things as rays; but, although light may consist of waves, it is not difficult to conceive the action of those waves to be in the direction of a straight line; and this straight line is to be considered as a ray.

The two most prominent optical qualities of light are reflection and refraction, of which the latter more narrowly concerns us, inasmuch as upon a true comprehension of its nature depends the right understanding of the whole theory of lenses.


Although light has been said to act in straight lines, the proposition only holds good for one homogeneous medium. Whenever two media of different densities come in contact, we have immediately an indication that light may be deflected—*refracted*, as it is called, from the straight line.

There are many satisfactory experiments for demonstrating this effect; one, and a very pretty one, is as follows:—



Suppose the accompanying diagram to represent a basin in which is placed a small object, say a coin. Now, the conditions being such,


Fig. 1.

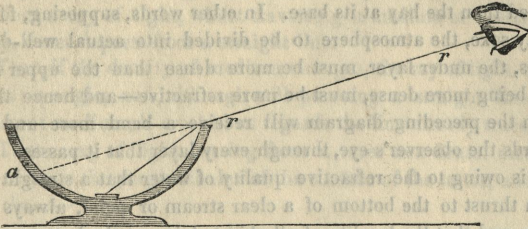

and an observer being placed as represented by the eye, the coin will be invisible, because the ray of light,  $r r$ , will impinge on the side of the basin,  $a$ . If, however, water be now poured into the basin, all other conditions remaining exactly the same, the coin will be made visible; simply because the water has the property of bending or refracting from its original direction the ray  $r r$ , and causing it to impinge in the direction of the dotted line.

Again, it is owing to the same operation of refraction, but through a different medium, that we see the sun after that luminary has descended below the level of the horizon. :—

Fig. 2.

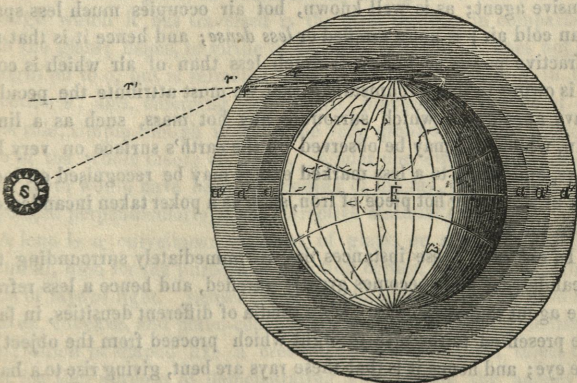

The earth, as is well known, is surrounded by an atmosphere

extending some forty-five miles high; and it is evident that the upper part of the atmosphere must be less compressed than the lower part—just as the hay in the upper part of a stack is less compressed than the hay at its base. In other words, supposing, for simplicity sake, the atmosphere to be divided into actual well-defined layers, the under layer must be more dense than the upper layer; and, being more dense, must be more refractive—and hence the ray  $r r$  in the preceding diagram will receive a bend more and more towards the observer's eye, through every layer that it passes.

It is owing to the refractive quality of water that a straight stick, when thrust to the bottom of a clear stream or pond, always looks bent; and that the locality of all objects lying at the bottom of vessels of water is so deceptive to the eye. It is owing to the same quality, also, that none of the heavenly bodies, except such as are directly over the observer's head, are ever seen in their true position; for the same refractive agency which enables us to observe the sun when he has already sunk below the horizon would also enable us to see a star, or, in short, any other luminous body, as under similar conditions.

I have already said that the upper portions of the atmosphere are less refractive than the lower portions, because they are less dense, and that they are less dense because less *compressed*.

Now—from whatever cause the lessening of density may arise, the effect on light will be the same. Thus, for instance, heat is an expansive agent; as is well known, hot air occupies much less space than cold air; is more rarefied or *less dense*; and hence it is that the refractive power of hot air is much less than of air which is cold. It is owing to this circumstance that we must attribute the peculiar wavy appearance which surrounds any hot mass, such as a lime-kiln, which also may be observed on the earth's surface on very hot days, and which to a less marked extent may be recognised on looking at a glowing hot piece of iron, such as a poker taken incandescent from the fire.

In either of these instances the air immediately surrounding the incandescent body becomes greatly rarefied, and hence a less refractive agent than originally. Two media of different densities, in fact, are presented to the rays of light which proceed from the object to the eye; and hence it is that these rays are bent, giving rise to a halo-like confusion or mixing of light all round the heated body.


Many other familiar illustrations of the property of refraction might be adduced, but these will be enough for my purposes. The following laws, then, as regards refraction may be laid down:—

1. That a ray of light, whilst traversing a medium of unvarying density, never departs from a straight line.

2. That, if the density of medium changes, the ray of light turns away at an angle, and, although still pursuing a straight line, for the present medium, is crooked as regards the line already traced.

3. That a ray of light passing from a rarer to a denser medium bends towards the perpendicular of the surface of the latter, and *vice versa*, thus:—

Fig. 3.

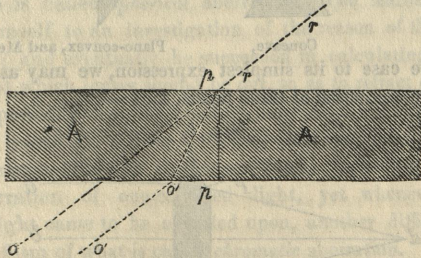


A is a block of glass, on which the ray of light  $r r$  falls; the air through which it has traversed is the rarer medium in comparison with the glass; hence, in virtue of the third law, the ray does not go straight on to  $o$ , but is refracted towards the perpendicular  $p$ , in the direction  $o'$ , and, emerging into the air, proceeds to the point  $o''$ . This rule, simple though it be, is the very groundwork and foundation of the whole theory of lenses. Under one circumstance, however, there would have been no bending of the ray, namely, if it had impinged perpendicularly to the refractive material's surface.

A lens is a curvilinear segment of glass, or other transparent material, used for the purpose of effecting certain refractive distributions of rays of light. Lenses are of various shapes; thus we have the convex, concave, and plano-convex lenses; there is also the meniscus lens, which is shaped like a crescent; of which we will select the first for the purpose of demonstrating how simply the agency of lenses is comprehended by reference to the law of refraction. Now,

the convex lens which I propose to investigate may clearly be regarded as an assemblage of many small facets or planes; and,

Fig. 4.

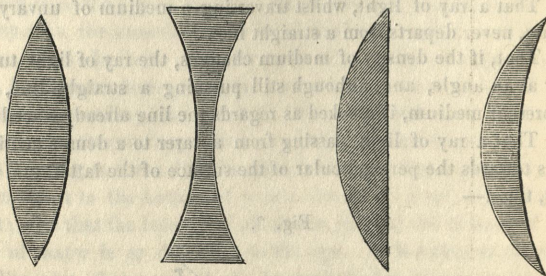


Convex,

Concave,

Plano-convex, and Meniscus lenses.

reducing the case to its simplest expression, we may assume each surface to be composed of three facets, thus:—

Fig. 5.

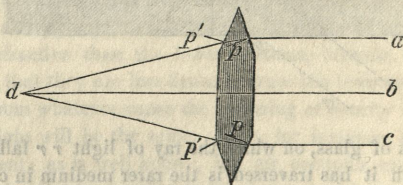


Now, let us examine what should be the result according to the laws of refraction, already laid down on the rays of light,  $abc$ , permitted to fall upon our representative of a double convex lens. In the first place, it is clear that the middle ray  $b$ , should not be refracted at all. It should go straight on, because it falls on the middle facet of the lens perpendicularly to its surface. But, as for the other rays, they fall respectively on their corresponding facets, each at an angle. Hence, if the law already laid down be true, they should be refracted or bent towards the point  $d$ , which we find to be the case.

It is found in practice that, even if the light with which we operate be monochromatic or one-coloured light—still all lenses which are made out of sections of spheres, do not cause the rays to converge to an exact focus; but only yield an approximation to this result, as is indicated by the accompanying diagram, from a consideration of

which it will be seen that the rays which pass through the edges of the lenses are the most refracted of the lot,—are those which most widely wander from the desired focus or point.


Fig. 6.

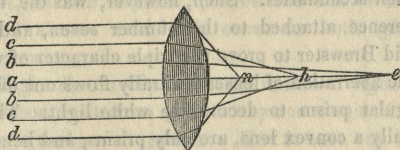

Now, this scattering of *one-coloured* rays by lenses cut out of spherical forms is called *spherical* aberration. The learned Descartes devoted himself to an investigation of the reason of this spherical aberration; and eventually he succeeded in calculating the proper oval out of which lenses should be cut, so as to refract one-coloured light to a perfect focus. In practice, however, the additional trouble of making lenses out of these Cartesian ovals was found not worth the pains; because, although they succeeded in correcting mere spherical aberration of one-coloured light, yet whenever white or coloured light came to be operated upon, another difficulty sprung up in the form of what is called *chromatic* aberration.

It was said by Newton,—and the expression was very generally employed up to our own days,—that white light might be decomposed into seven primitive colours—*red, orange, yellow, green, blue, indigo, and violet*, as indicated by the accompanying diagram.

Fig. 7.

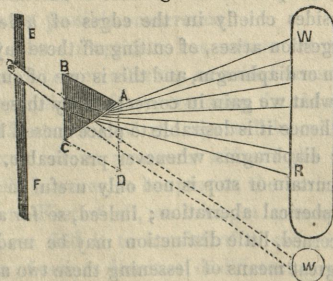

It is not a little strange that Newton should have failed to

discover the now well-known fact to us, that the prismatic spectrum does not present us with seven, but with only three, primitive colours—*red*, *yellow*, and *blue* :—which, by being combined amongst themselves, give rise to green, orange, indigo, and violet, as their secondaries. Such, however, was the fact; a sort of mystic reverence attached to the number seven, and it remained for Sir David Brewster to prove the triple character of white light.

Chromatic aberration of lenses naturally flows out of the property of a triangular prism to decompose white light. The edges of a lens, especially a convex lens, are only prisms, and hence they must naturally produce a prismatic decomposition of light.

The two aberrations—namely, spherical and chromatic, are the two great difficulties which optical instrument-makers have to encounter; nevertheless, by taking advantage of certain facts, and by proceeding with care, they may be, by a series of compensations, almost entirely overcome. Now, this conquering of spherical and chromatic aberration in optical instruments is really a great achievement, when we consider that the illustrious Newton pronounced the task, in his opinion, hopeless.

I do not think it necessary, on the present occasion, to go minutely into the means which opticians have recourse to for the overcoming of spherical and chromatic aberration. A few general remarks on these subjects will be all that I shall here make, reserving a more detailed account when treating of the various forms of photographic lenses.

In the first place, then, it will be observed, by reference to preceding diagrams, that, so far as the error of chromatic aberration is concerned, it resides chiefly in the edges of a lens; hence the most natural suggestion arises, of cutting off these rays altogether by means of a curtain or diaphragm, and this is one of our most frequent resources. But what we gain in correctness by these means we lose in illumination; hence it is desirable to place oneself beyond the necessity of using diaphragms whenever practicable. I must here remark that the curtain or stop is not only useful in lessening chromatic but also spherical aberration; indeed, so far as remedial resources are concerned, little distinction may be made between the two. The next great means of lessening these two aberrations consists in availing ourselves of a property not known to Newton;

otherwise he would never have spoken so despondingly concerning the manufacture of achromatic instruments. It is this—that different kinds of glass have different powers of refrangibility on the same coloured light, and thus, by making a lens of different kinds of glass, in the required proportions and of the required curves, we can almost completely overcome both spherical and chromatic aberration.

This very slight sketch of the general nature of light will suffice for an introduction to the true part of my communication—the art of making photographic delineations. Had it been my intention to write a treatise on optics, I must have gone far more into detail.


I cannot, however, leave the subjects of spherical and chromatic aberration without alluding to the beautifully efficient methods nature has had recourse to for overcoming these difficulties in the eyes of animals. I speak now of the eyes of man, and other mammalia; for, on descending into the lower orders of animal life, the structure of the eye becomes far more simple than any one except a naturalist would imagine.

From what we have said of chromatic aberration, it is quite evident that, were it not completely overcome by adequate provision in the human eye, we could never have seen a white object, or, rather, we could never have seen it in its true colour of white. Its edges would be surrounded with a halo of iridescent light; and every attempt at truthful observance of colour would have been fruitless. Now, I need scarcely say that the difficulty has been so completely overcome, that, notwithstanding all the long list of diseases to which the eyes of human beings and animals are subject, chromatic aberration is of the rarest possible occurrence.

So completely like an optician has nature set to work in her fabrication of eyes that, even after my curtailed account of the means had recourse to by opticians for overcoming the chromatic difficulty, the rationale of the structure of the eye will be evident on viewing a sectional diagram of its structure without the necessity of an explanation. Still, however, to be precise, the various provisions of nature are these:—First of all, on taking a general survey of the ocular structure, we find it to consist of a collection of different transparent media of various densities, of different curves, different refrangible properties; we have in the iris a contrivance which is the

precise counterpart of the black stop or curtain used by opticians for cutting off external rays; and, carrying our examination more

Fig. 8.

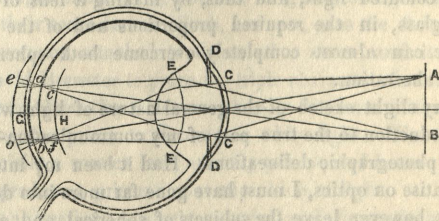


closely, we find that the various humours or lenses, instead of being strictly spherical, are constructed out of curves more proper for avoiding aberration. And, not content with adopting the adjuncts of Cartesian curves, compound lenses, and the optician's stop, nature has gone farther still, and, in the beautiful contrivance of an enlarging and decreasing aperture which we find in her iris or stop, she employs a mechanism so wonderfully refined that man would vainly endeavour to adopt it for his optical instruments. With regard to the iris of eyes, I may observe that the general notion of its use is merely as a means of cutting off an excess of light, and thus tempering the vision to the varieties of illumination to which it is exposed. Undoubtedly this is one use of the iris and its moveable pupil, and indeed its greatest use; but, collaterally, it also acts as one means in nature's optical economy of preventing any chance of spherical and chromatic aberration.

Before proceeding to explain the peculiarities of that portion of a ray of light which produces the greatest photographic or chemical effect, I would point out some of the necessary consequences resulting from that principle of refraction already explained, more particularly with respect to the formation of images or representations of natural objects by means of lenses. When a convex lens is directed towards a luminous object placed at an infinite distance, as the sun for instance, a bright and luminous spot will be observed on a piece of paper held at a certain distance behind the lens. Now, this spot is called the principal *focus*, or *focus* of parallel rays of the lens; and its distance from the lens the *focal length*, which depends upon



the convexity of the lens; the greater the amount of convexity the shorter the focus. In the accompanying figure D D may represent a lens, and C A E parallel rays of light, which, on passing


Fig. 9.



the lens, will be refracted, and, by meeting, form a focus at F.

Again, if the lens be directed towards an object the rays from which are not parallel but divergent, as is the case with objects at a short distance, the focus F, or the point where the rays meet, will be at a greater distance from the lens, and a sheet of paper held at that point will show an *inverted image* of the object; and, if the distance of the object from the lens be made to vary, it will be found that the nearer it is to the lens the greater the distance the sheet of paper requires to be held behind the lens to get a clear representation of the object, and *vice versâ*. This will, perhaps, be better understood by reference to the following cut:—

Fig. 10.

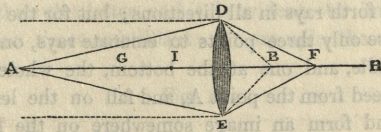


Let the dotted lines represent parallel rays of light falling on the lens D E, and refracted to the principal focus B, and let A D, A E, be rays diverging from the point A, they will converge after passing the lens towards the point F, where they intersect each other, and form an image of the point A; and, if the lens be brought nearer to the radiating point A, the focus F will be lengthened, and *vice versâ*. These alterations in the focal distance follow certain rules; for suppose the point A to be placed at G, a point equal to twice the principal focal distance C B, the focus F will be at H, as far behind the lens as the radiant point G is before it. If A be placed at I, the focus will be infinitely distant, or the refracted rays will become parallel, and will not form an image; finally, if A be

placed between I and C, the rays diverge after refraction. Either of the points A or F may be considered as the focus, for, if the radiant point be F, its image will be formed at A, in the same way that A will produce an image or focus at F; it is to this relation or interchange between the radiant points and foci that the term has been given of *conjugate foci*.

The formation of images in that well-known instrument, the *camera obscura*, is due to a convex lens placed in the front of the instrument. It has been before mentioned that all images formed by a convex lens are reversed, and consequently inverted. Now, the reason of this, and also of the formation of an image, will be better understood by referring to the following cut:—

Fig. 11.

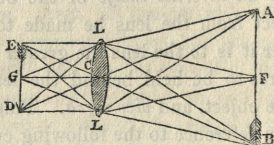

If A F B is an object placed before a convex lens, L L, every point of it will send forth rays in all directions; but for the sake of simplicity, suppose only three points to emanate rays, one at the top, one at the middle, and one at the bottom, the whole of the rays then that proceed from the point A, and fall on the lens L L, will be refracted and form an image somewhere on the line A C D, which is drawn direct through the centre of the lens; consequently the focus D, produced by the convergence of the rays proceeding from A, must form an image of A, only in a different relative position; the middle point F, being in a direct line with the axis of the lens, will have its image formed on the axis, G, and the rays proceeding from the point B will form an image as E; so that by imagining luminous objects to be made up of an infinite number of radiating points, and the rays from each individual point, although falling on the whole surface of the lens, to converge again and form a focus or representation of that point from which the rays first emerged, it will be very easy to comprehend how images are formed, and the cause of those images being reversed.


It must also be evident that in the two triangles,  $A C B$  and  $E C D$ , that  $E D$ , the length of the image, must be to  $A B$  the length of the object, as  $C D$ , the distance of the image, is to  $C A$  the distance of the object from the lens.

This last rule will point out the method to be followed if images are required of a certain determinate size; for example, if  $C F$  was equal to  $C G$ , the image  $E D$  would be of the same size as the object  $A B$ ; if  $C F$  was as long again as  $C G$ , the image would be half the size of the object; if, on the contrary,  $C F$  was half the length of  $C G$ , the image  $G D$  would be double the size of the object  $A B$ .

A knowledge of this principle is of some importance, inasmuch as the relative sizes of the image and object can be determined beforehand, and thus allowing more extended applications to be made of those instruments by means of which photographic pictures are obtained.

If two lenses be used of the same focus, the images produced by one may be rendered much more brilliant than those produced by the other, by having the former of larger diameter; for instance, if one of the lenses was two inches and the other one inch in diameter, the former would intercept four times the quantity of light more than the latter, and it is evident the image produced would be four times as brilliant; for example, the cone of light,

Fig. 12.



$A B C$ , in the accompanying figure, would be entirely intercepted by the lens  $B C$ , while the lens  $D E$  would only intercept a small part; so, when it is not possible to increase the brightness of the object by illuminating it, the brightness of the image can always be increased by using a larger lens.

Care must be taken not to confound *brightness* with clearness;

they are two things totally different, and the gaining of one does not in general depend upon the other; for it is necessary, in many cases, as before explained, when treating of spherical and chromatic aberration, to stop a portion of light from falling on the lens, by which means a much sharper picture is obtained.


When a ray of white light, as emanated by the sun, is decomposed by being passed through a prism, as before explained at fig. 7, into its primitive colours, it was discovered by Sir William Herschel that the different colours of the spectrum possessed different heating powers. This he ascertained by means of a number of thermometers which he placed at different parts of the spectrum, when he found that the heating power of the rays gradually increased from the violet, where it was the least, to the extreme red; and that the maximum temperature existed at some distance beyond the red, and out of the visible part of the spectrum. This discovery led to the inquiry, whether the chemical effect produced by light on some bodies, especially some of the compounds of silver, was due to the heat accompanying it, or to some other cause. This investigation has engaged the attention of several modern philosophers, among whom may be named Mr. R. Hunt and Sir J. F. W. Herschel, who have demonstrated that the chemical effects of light are not due to the heat present in the rays, but follow an entirely different law, being greatest at the violet end of the spectrum when the heating power is least, and least at the red when the heat is the greatest.

The fact is easily demonstrated by causing the prismatic spectrum to fall on a sheet of paper impregnated with chloride of silver, when the paper will become blackened at the violet end, and even beyond any visible rays of light, and the effect gradually decreasing as we approach the red. This and several other experiments of a like character have given rise to the idea that there must be some peculiar fluid accompanying light which produces all the chemical changes we notice are produced by light in our photographic experiments. The terms *energia* and *actinism* have each been proposed as a name for this supposed fluid; and, although both are open to the objection of not being sufficiently definite in their signification, the latter term, actinism, is the one now usually adopted.

Light may, therefore, be said to be made up of three separate and

distinct fluids, producing actinic, luminous, and heating effects, and the relation of these to each other is shown in the following cut:—

Fig. 13.

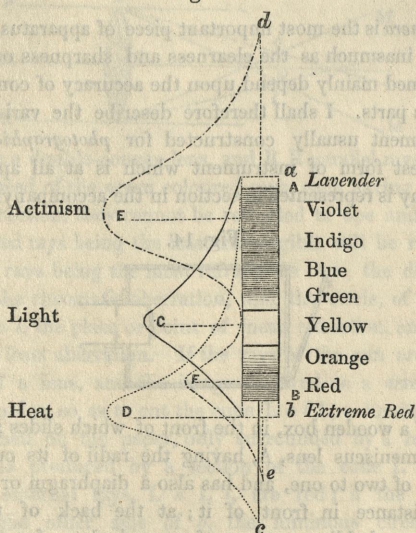


The shaded portion represents the colours as they occur in the decomposed solar beam; and the curved lines the relative amount of *actinism*, *light*, and *heat*, which in the case of *Actinism* is greatest at E, and ceases at *d* and *e*, having a slight increase, however, at F, which may be due, according to some experiments of M. Claudet, to the yellow rays, being not merely negative in their action, but having a positive destructive influence on the effects produced by actinic rays. *Light* is most intense at C, and ceases altogether at *a* and *b*; and *Heat* is greatest at D, disappearing at *a* and *c*.

## PHOTOGRAPHIC APPARATUS, MATERIALS, &amp;c.

The *Camera* is the most important piece of apparatus to the photographer, inasmuch as the clearness and sharpness of the results to be obtained mainly depend upon the accuracy of construction of the various parts. I shall therefore describe the various forms of this instrument usually constructed for *photographic* purposes. The simplest form of instrument which is at all applicable for photography is represented in section in the accompanying cut, and


Fig. 14.

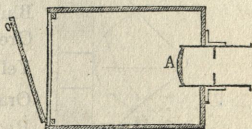

consists of a wooden box, in the front of which slides a brass tube holding a meniscus lens, A, having the radii of its curves in the proportion of two to one, and has also a diaphragm or stop placed a short distance in front of it; at the back of the camera slides a frame holding a piece of ground glass, for the purpose of ascertaining the focus, and also a frame so constructed that the prepared paper can be placed between a plate of glass and a smooth surface of wood or slate; in the front of the glass is a slide to protect the paper from the action of light till introduced into the camera. In using cameras which have either meniscus or plain lenses, it must be borne in mind that the visual focus, as shown on the ground glass, will not give a sharp photographic picture, and the reason of this is very obvious—for those rays which produce a chemical action on any sensitive surface or material always accompany the violet rays of the spectrum; and, as the violet rays form a focus nearer to the lens than that requisite to give the best visual focus, the lens, therefore, must be approximated to the paper or prepared surface, so that it may be brought to that point where the violet and chemical rays form a focus. Although I have before explained the peculiarity of chro-

matic refraction, its application to the camera may be better understood by the following diagram:—


Fig. 15.

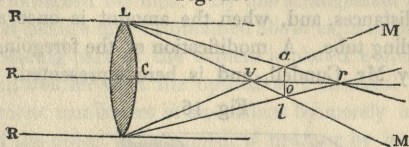

If  $L L$  be a double-convex lens, and  $R R$  parallel rays of white light, composed of the seven coloured rays, each having a different *index* of refraction, they cannot be refracted to one and the same point; the red rays being the least refrangible will be refracted to  $r$ , the violet rays being the most refrangible to  $v$ ; the distance  $v r$  constitutes the chromatic aberration, and the circle, of which the diameter is  $a l$ , the place or point of mean refraction, and is called the circle of least aberration. If the rays of the sun are refracted by means of a lens, and the image received on a screen placed between  $C$  and  $o$ , so as to cut the cone  $L a l L$ , a luminous circle will be formed on the paper, only surrounded by a red border, because it is produced by a section of the cone  $L a l L$ , of which the external rays,  $L a L l$ , are red; if the screen be moved to the other side of  $o$ , the luminous circle will be bordered with violet, because it will be a section of the cone  $M a, M l$ , of which the exterior rays are violet. To avoid the influence of spherical aberration, and to render the phenomena of colouration more evident, let an opaque disk be placed over the central portion of the lens so as to allow the rays only to pass which are at the edge of the glass, a violet image of the sun will be seen at  $v$ , red at  $r$ , and finally images of all the colours of the spectrum in the intermediate space; consequently, the general image will not only be confused, but clothed with prismatic colours. To obtain the clearest representation to the eye of any object placed before the lens  $C$ , the screen of ground glass must be placed at  $a l$ , but to produce a sharp photographic picture the prepared paper must be placed nearer to the lens at  $V$ , or, what is equivalent, the lens adjusted nearer to the paper. The distance the paper ought to be approximated to the lens, after ascertaining the optical or visual


focus, will depend, in a great measure, upon the focal length of lens, and the distance of the object. The best plan to arrive at this point is to make one or two trials with the camera upon objects at different distances, and, when the amount is once ascertained, mark the sliding tube. A modification of the foregoing has been suggested by Mr. Cundell, and is here represented. The chief

Fig. 16.

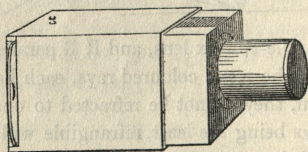

novelty in this arrangement is the introduction of two diaphragms within the body of the camera, and in the elongation of the brass front, both of which are useful in protecting the picture from all external light, except that which emanates from the objects to be copied.

Fig. 17.

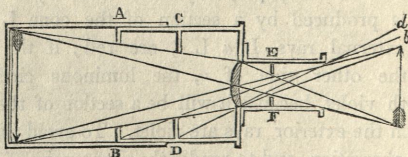

By reference to Fig. 17, which shows this form of camera in section, it will be seen, that by means of the diaphragm, or "stop" E F, the rays from the barb of the arrow are excluded from the upper, and received only upon the lower half of the lens, at which they fall at a comparatively high and *equal* angle of incidence. They are thus less refracted than they would otherwise be, and their focus is not only sharpened, but elongated. By this means the picture, instead of being formed in the usual curve, is formed much nearer to a straight line in the plane of the prepared surface placed to receive it.

A lens of twelve inches focus, which is the kind most recommended, ought to have an aperture of 2-4 inches. The diaphragm




at E F (in which the principal virtue of the instrument resides) should be placed 1-5 inch in advance of the lens, and its opening ought not to exceed 1-2 inch. By this arrangement a pretty sharp and distinct picture may be obtained about eight inches by six.

On the sliding part of the camera is placed a strip of wood or ivory, graduated for both the optical and chemical focus, so that the instrument can be set in an instant by merely measuring the distance of the object to be copied, if near, or by guessing at it, if out of reach.

The foregoing are the best forms of camera at present constructed with plain lenses; there is, however, another form of camera, which was patented by Mr. Beard, in which a concave reflector is employed to produce the picture, but which, being so small compared to the size of the apparatus, renders it of comparatively little use.

The only construction of camera which is calculated to produce the most finished and perfect photographs is that in which an achromatic lens is employed. The achromatic lens is either single or compound; the single is usually employed for views, and the compound for portraits.

Fig. 18.



The usual form of camera fitted with a single achromatic lens is shown in the accompanying cut. It consists of a mahogany box, in the front of which is fixed a brass sliding tube A, having an achromatic lens at one end, and the opening contracted, so as to form a stop at the other, as shown at B. In the front of the stop is a small shutter for opening or closing the aperture. At the back of the camera fits the ground glass for ascertaining the focus and frame for holding the prepared plate or paper.

The reason why the single achromatic lens is usually employed for views and other inanimate objects is that the time required to produce the picture is not limited, whereas in the case of portraits

it is of great moment to obtain a result in the shortest possible time. This is accomplished by the employment of a combination of achromatic lenses.

Both Chevalier and Lerebours, in France, and Voigtlander, in Germany, have paid great attention to the construction of these compound lenses, and till lately were the only manufacturers who could supply a compound lens properly constructed. But now, in consequence of the great demand for the best description of lenses for photographic purposes, there has been great pains bestowed in England, both upon the manufacture of the glass of which the lenses are made, and also to ascertain the best curves, &c., to which they ought to be worked. The result has been the production of glasses equal in every respect, and, in many instances, superior, to those imported from the continent, and at a much less cost.

Fig. 19.





Fig. 20.



The above cuts represent a camera fitted with one of these compound lenses, and also an enlarged view in section showing the disposition of the various lenses &c., and, when properly constructed, will be found the most effective and useful lens for photographic purposes that can be obtained, as it forms either a short or long focus as desired. It is furnished with a moveable brass cap D, and a series of stops or diaphragms C, which are employed when the lens is used for taking views and sometimes portraits when the light is very brilliant.\* When a long focus lens is required, as is usually the case for views, the back lens A is removed, and the cap D, and stop C, substituted in its place, and the whole of the

\* The size of stop to be employed must be left to the judgment of the operator, who will be guided by the time in which he desires the picture to be obtained, and also the character and arrangement of the objects to be represented; the smaller the stop the longer the time required, but the sharper and more distinct the picture.

brass mounting and the lens is reversed with respect to the camera by the screw over the lens B, by which arrangement the lens B is placed within the camera and is capable of being adjusted by the same rackwork as when the combination is employed.

Fig. 21.



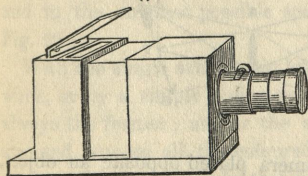


Fig. 22.

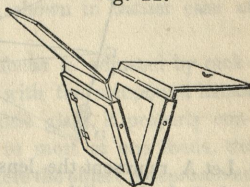

The most complete and convenient form of rigid camera is that represented in the above cut; it consists of two portions, one sliding within the other, by which either a long or short focus lens can be employed, and in the groove at the back is adapted either a frame for prepared silver or glass plates of various sizes, or one of Horne and Co.'s improved double frames for holding two sheets of prepared paper in the space usually occupied for one, as shown at Fig. 22.


Fig. 23.



In some instances it is required to obtain representations of objects at a short distance from the camera and whose position varies very considerably from a vertical plane, in which case the form of camera represented above is employed, which has a mechanical contrivance at the back, whereby the relative position of the plate to the lens can be altered. This arrangement allows a lens of very short focus to be used, as the errors caused by various parts of the object to be copied being at different distances is, in great part, remedied by altering the parallelism of the back frame and the object-glass. This effect will be better understood by reference

to the following diagram, Fig. 24, and what has been before explained relative to conjugate foci at page 11.



Fig. 24.

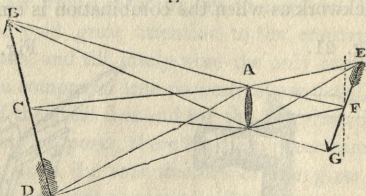

Let A represent the lens of camera placed opposite an object, B, C, D, in the position represented—it will be evident that the only point where a correct focus would be obtained on a vertical plane, represented by a dotted line, would be at F, but by shifting the position of the back to E, F, G, as shown in the cut, the whole of the object may be brought into focus.

Fig. 26.

Fig. 25.

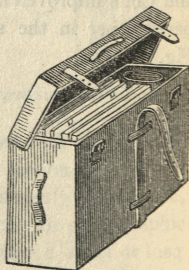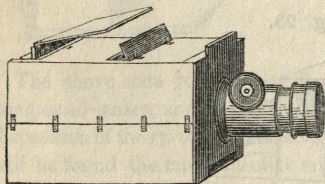

The most useful and complete camera for general photographic purposes, and especially adapted for tourists from its extreme portability, combined with lightness and strength, is that represented ready for use at Fig. 25. The front of the camera holding the lens has a vertical adjustment, which enables the relative proportion of foreground or sky in the required picture to be altered without disturbing the position of the camera. In the body of the camera is placed two or more openings or slides, by which either the long focus lens for views, or the shorter combination for portraits, &c. can be employed as desired. When not required for use, the lens

is unscrewed, the front and slides lifted from their grooves, and the body of the camera folded together by the hinges shown in the cut, by which arrangement the camera box, together with the slides for prepared paper, glass, or silver plates, frame for ground glass, achromatic lens, &c., can be conveniently packed, and in the smallest possible space, as shown in leather case at Fig. 26.

With the single achromatic lens, the focus is adjusted by rack-work, or by a simple sliding tube, but with the compound lenses always the former; and as the achromatic glass, if properly constructed, causes all the coloured rays to meet at one focus, the correct adjustment will be that point where the object is represented in the clearest and sharpest manner on the ground glass. This is ascertained by throwing a piece of dark calico or other material over the head and back of the camera which, by shading the light, allows the picture to be seen on the ground glass; but by far the most correct method is by using a short conical tube, having a magnify-




ing glass at its upper end, as represented at Fig. 27. The wide part is placed on the surface of the ground glass, and the eye, being placed at the other end, perceives a magnified representation of any required portion of the picture, by which means the requisite sharpness of outline is more easily and correctly obtained than by any other method.

Fig. 28.



Fig. 29.



As all objects in the camera obscura appear reversed, that is, all right-hand objects will appear to the left in the picture, and *vice versa*, it is of great importance in the daguerreotype process to obtain the pictures as they appear in nature; this is accomplished by the small reflecting mirror or prism, Figs. 28 and 29, which have the effect of again reversing the object in the camera,

and thus rendering the picture correct. When used they must be turned towards the object to be copied till a perfect representation is observed on the ground glass.

Fig. 30.




Fig. 31.





Fig. 32.



Fig. 33.



For the purpose of directing the camera towards the object to be copied, and keeping it steady during its employment, a variety of stands or supports have been contrived, the most convenient forms of which are represented above. Fig. 30 is constructed of three triangular legs, attached at the top to a brass ball and socket-joint, and which is adapted, when required, by a screw-plate to the bottom of the camera; it is a very portable stand, and answers its purpose remarkably well if the camera be of small dimensions; if required for a large sized instrument, the forms represented at Figs. 31, 32, and 33, will be found the best. Fig. 31 is of the simplest and cheapest construction of table stand, but is wanting in portability, and only possesses one adjustment for the purpose of altering the direction of the camera. Figs. 32 and 33 are the firmest and most convenient form of stands, possessing all the requisite adjustments; the former being best adapted, from its portability, for the use of tourists and travellers, the latter from its convenience for home use.

The various forms of apparatus, &c., which are required for specific photographic processes will be best described when treating of these processes; but the photographer will find the commencement of his progress much facilitated by possessing some few of those articles which are constantly being employed, and making himself familiar with their use, the chief of which are:—A pair of scales, the pans of which should be of glass, and a set of weights

from 1 oz. to 1 grain; a graduated glass measure or two, **Fig. 34.** to contain about 2 fluid ounces, and a smaller one graduated into drops; and care should be taken that these glasses are perfectly smooth at the bottom, for the convenience of being cleaned out each time of using; and when measuring a quantity the measure should be raised about level with the eye, by which the correct amount is easily determined; a few glass rods about 9 inches long, perfectly smooth and cylindrical, for the purpose of mixing and applying various solutions, and other purposes; a glass flask or two for making and heating solutions; a few glass funnels and conical-lipped glasses of various sizes for filtering solutions of silver, hyposulphite of soda, &c., and receiving the solutions when filtered. The arrangement for filtering is shown at **Fig. 35.**


**Fig. 35.**

**Fig. 36.** A funnel and receiving glass of the required sizes are arranged as shown in cut; a circular piece of filtering or bibulous paper is folded in half twice, so as to form, when opened, a kind of paper cone, as represented at **Fig. 36;** this is placed within the funnel, and the solution to be filtered, supposed to be in a flask, is poured in a gentle stream against the doubled side of the paper cone; this is best and most neatly



performed by applying a moistened glass rod to the edge of the vessel from which the fluid is to be poured, and placing the end of it so that a slight inclination of the flask or other vessel will cause a slender stream to flow down the rod against the side of the paper cone without the danger of breaking the paper or spilling the fluid; a small spirit-lamp for heating solutions, and an oil or candle lamp, surrounded with a yellow or red glass shade, will be found extremely convenient, as affording sufficient light for manipulation, at the same time producing no sensible effect on any prepared surfaces of metal, glass, or paper. For the purpose of making the various solutions, distilled water should alone be used, and care must be taken not to employ distilled water containing the smallest quantity of any organic substances, such as essential oils, &c., which would speedily cause solutions of silver,—solutions chiefly used for photographic purposes—to become decomposed and useless. Where pure distilled water cannot be obtained the requisite quantity can very easily be manufactured by means of a portable still, represented by the accompanying cut.

Fig. 37.

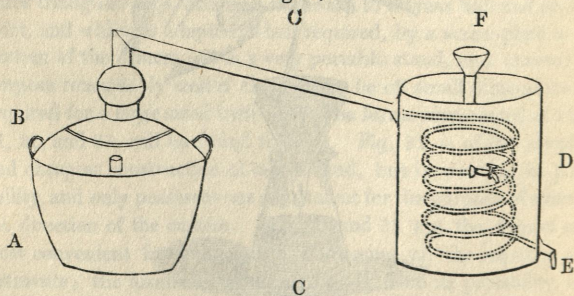

The body A contains about a gallon of water, to be introduced through the opening, which is afterwards closed with a cork:—it is then placed over a gentle fire, and the worm-tub placed on a convenient support connected with it by means of an intermediate tube, the joints being rendered steam-tight by two short pieces of vulcanized indiarubber tube. The worm-tub being filled with cold water condenses the steam as produced, and the distilled water runs off at the opening E. As the water becomes hot it is drawn



off by the stopcock D, a fresh quantity of cold water being poured into it by the funnel F, which reaches to the bottom of the tub. A very pure water, and quite equal to distilled, can be obtained by melting a clean and clear piece of ice, the Wenham Lake ice being the best for the purpose.

The best substitute for pure water, and what is quite equal to it for many of the processes where a considerable quantity is required, as in washing out the salts of silver, &c., in preparing iodized paper, setting paper positives, &c., is made by boiling rain or soft river water, allowing it to cool, and then carefully filtering it.

#### CHEMICALS.

*Nitrate of Silver.*—This salt, which is prepared by dissolving pure silver in nitric acid, and evaporating the solution till crystals are obtained—should only be purchased in the form of crystals;—not in the form of sticks, which are the common fused *lunar caustic* of the shops, and which generally contains impurities detrimental to its employment as a photographic agent. The crystals should be of a white colour, and perfectly free from any smell of nitric acid; should this, however, be present, the crystals must be dissolved in some distilled water, evaporated, and crystallized.

*Iodine.*—This substance is obtained from the ashes of seaweed called kelp, which being lixiviated with water and all the crystallizable salts being separated, the mother liquid which remains is mixed with oxide of manganese and sulphuric acid, in a glass retort or other convenient vessel, and exposed to heat, when iodine rises as a fine violet-coloured vapour, which condenses in the form of steel-grey opaque crystals. When pure, and fit for photographic purposes, the crystals should be well formed, and perfectly free from moisture.

*Bromine.*—This is extracted by a similar process to that just described for iodine, from the mother liquor of sea water (bittern). It condenses in the form of a dark red-looking liquid, very volatile, giving off a dark red vapour of a powerful and suffocating odour. It is best preserved in a well-stopped glass phial containing a small quantity of water, which, from its less specific gravity, floats on its surface, and, in a measure, prevents its evaporation.

*Iodide of Potassium.*—This salt is commonly prepared by satu-

rating a solution of pure potass with iodine, evaporating to dryness, and fusing the product, which is afterwards dissolved in water and crystallized, when it forms cubical crystals of a white colour. When pure it should not be very deliquescent; its solution in water should not effervesce on the addition of a few drops of a dilute acid, and should be perfectly soluble in alcohol.

*Bromide of Potassium* is prepared by mixing bromine and solution of pure potass together, and evaporating to dryness. It dissolves readily in water, and crystallizes in small cubes.

*Acetic Acid*.—This is manufactured on the large scale by saturating the acid liquor obtained by the distillation of wood in iron cylinders, with lime or chalk. The solution of acetate of lime formed is decomposed by sulphate of soda, with the formation of insoluble sulphate of lime and soluble acetate of soda, which latter is separated by filtration, evaporated to dryness, and distilled with sulphuric acid in earthen or glass retorts, when acetic acid passes off, and is subsequently purified by redistillation. When required for photographic purposes it should be very carefully distilled, to prevent the formation of sulphurous acid, a substance very detrimental to its proper action; and it should also be of sufficient strength to become quite solid or crystallized when the vessel containing it is placed in ice, from which circumstance it is commonly called glacial or crystallizable acetic acid.

*Gallic Acid*.—This acid is obtained from the nutgall, and may be prepared by allowing a mixture of powdered galls and water, of the consistency of thin paste, to be exposed to the action of the atmosphere, at a temperature between  $60^{\circ}$  and  $70^{\circ}$ , for about four or five weeks; making up from time to time what may be lost by evaporation by the addition of small quantities of water; at the end of this period the whole mass, which will have become mouldy, is to be dried by pressing out the liquid;—the residue is now boiled in water, and the whole filtered while hot; the clear filtrate as it cools will deposit crystals of gallic acid, which may be further purified and improved in colour by boiling it with about 8 parts of water and a fifth of its weight of animal charcoal, and again filtering, when pure crystallized acid will be deposited as the solution cools. One ounce of water, at the ordinary temperature, will dissolve about four grains of gallic acid.

*Pyro-gallic Acid.*—A quantity of gallic acid placed in a glass retort is heated to a temperature between  $410^{\circ}$  and  $420^{\circ}$ , by means of an oil bath;—the pure pyro-gallic acid sublimes in the upper part of the retort in the form of brilliant white lamellar crystals, and a blackish deposit of meta-gallic acid remains in the body of the retort.

*Hyposulphite of Soda.*—This salt can be made by decomposing hyposulphite of lime by carbonate of soda; carbonate of lime precipitates, and hyposulphite of soda remains in solution. The hyposulphite of lime is prepared by boiling for two or three hours a mixture of two parts of sublimed sulphur, three parts of fresh-slacked lime, and 200 parts of water; then filtering the clear liquid, which will be of a deep yellow colour, from its containing persulphuret of calcium, into a large, open, and shallow vessel, freely exposed to the air;—the yellow colour of the liquid will gradually disappear from the absorption of oxygen, and when colourless will have become a solution of hyposulphite of lime. Hyposulphite of soda may also be prepared according to the following process given in No. 4 of the CHEMICAL RECORD:—Mix 1 lb. of finely-pulverized calcined carbonate of soda with 10 oz. of flowers of sulphur. Heat the mixture slowly, till the sulphur melts. Stir the fused mass, so as to expose all its parts freely to the atmosphere, whereby it passes from the state of a sulphuret to that of a hyposulphite. Dissolve in water, filter the solution, and boil it immediately with flowers of sulphur. On cooling, after being now filtered, it will deposit beautiful crystals of the hyposulphite.

## PHOTOGENIC DRAWING.

Although as far back as the year 1556 the blackening effect of light upon chloride of silver, or horn silver as it was then called appears to have been well known, it was not till upwards of two centuries had elapsed that we find any recorded attempts to apply this property to the production of photogenic impressions. In the Journal of the Royal Institution for June, 1802, we find a notice of some experiments of the celebrated porcelain-manufacturer, Joseph Wedgwood, and also of Sir Humphry Davy, from which it appears that both these philosophers succeeded in obtaining photographic pictures. Wedgwood, by washing over the surface of leather or paper with a solution of nitrate of silver, and placing over the prepared surface the object he wished to copy, found, on exposure to the sun's rays, that the light passed through the object in various degrees of intensity, according to the degree of transparency of its various parts, producing a corresponding blackening effect on the paper or leather beneath. Sir H. Davy also obtained impressions on paper prepared with nitrate of silver, by refracted light, by exposing it so as to receive the picture formed at the focus of a solar microscope; but, in consequence of no means being then known or discovered to prevent the further action of light after the impressions had been obtained, these important experiments, at that time, led to no conclusive result, and the subject was apparently abandoned. It was not till January, 1839, that we find a process published by which photogenic impressions could be obtained and afterwards rendered permanent. This process appeared in a paper sent to the Royal Society by Mr. Fox Talbot. The method he employed for obtaining impressions from leaves, flowers, feathers, &c., was by employing the ordinary chloride of silver paper, and fixing them by the use of common salt.


Since the discoveries of Mr. Fox Talbot, we find this interesting subject taken up by many lovers of science, who have not only discovered new processes, but also investigated the chemical changes and principles in their production. Amongst the foremost of these may be named Sir John Herschel and Mr. Robert Hunt,

to the latter of whom we are indebted for many very interesting photographic processes, termed by the inventor Ferrotypes, Energiatypes, Chromotypes, &c., and a valuable series of experiments on the chemical action of light, which may be found in his valuable "Researches on Light;" but, as it is my intention in these papers only to give such processes and manipulation whereby photographic pictures can be obtained in the greatest perfection and certainty, I must of necessity omit others which are not practically useful, although extremely interesting in connection with the science of photography.

To Sir John Herschel we owe the *Chrysotype*, in which iron and gold are employed; *Cyanotype*, in which impressions are produced by the salts of iron in combination with those of cyanogen; *Anthotype*, where the expressed juice, watery or alcoholic infusions of the petals of the wild poppy, stock, rose, &c., are demonstrated to be effaced by the action of light, showing that the vital principle of plants prevents those changes of colour and properties which immediately take place when that influence is destroyed; and many other most interesting experiments which would tend to prove that, although the compounds of silver are those which are generally used for photogenic or photographic purposes, and they appear, as far as our present knowledge extends, to be the most influenced by the action of light, it is extremely probable that there is not a compound, of whatever nature it may be, but is affected more or less by light; and although that effect may not, in many instances, be visible, still it may exist, and only requires the substance which has been exposed to its action to be placed under different circumstances to make the effect apparent to our senses.

To render paper sensitive to light it appears essential to have in the texture, or on the surface of the paper, a fixed salt or compound of silver moistened with a soluble salt, easily decomposed when in contact with organic matter, as the nitrate of silver, for example, which is very sensitive to light when in contact with the chloride, iodide, bromide, fluoride, &c., of silver; many of these compounds and their mixtures have from time to time been recommended for photographic purposes, and produce varied results, both as regards the colour of the picture and the time of its production. By reference to the following diagram the chemical changes that take place

when a chloride is mixed with excess of nitrate of silver may, perhaps, be better understood.

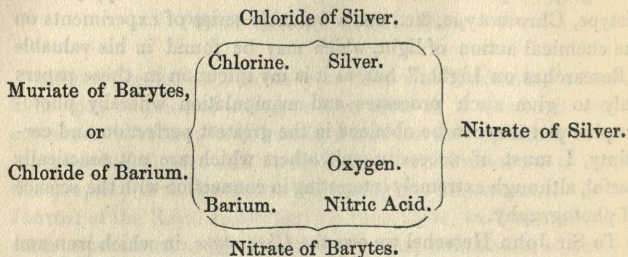

The paper being first moistened with solution of chloride of barium, and then placed in an excess of solution of nitrate of silver, the following changes of elements take place:—The chlorine of the chloride of barium combines with the silver of the nitrate, forming an insoluble chloride of silver in the paper, at the same time nitrate of barytes is formed by the union of the oxygen with the barium, producing barytes, which, combining with the nitric acid, forms a soluble nitrate of barytes, which is for the most part dissolved out in a subsequent process, leaving the chloride of silver moistened with the excess of nitrate of silver, which, as before mentioned, is the most favourable condition to receive photogenic impressions.

I shall now describe the best and simplest process for preparing photogenic paper with which I am acquainted; and first with respect to the

#### SELECTION OF THE PAPER.

The kind of paper I have uniformly found the best suited for the purpose is that sold as manufactured by "Carson Freres;" if this description of paper cannot be obtained, the blue wove post manufactured by Whatman will produce very good results. The paper should be cut into sheets of a convenient size for manipulating, about 9 inches by 8, and those sheets only are to be employed which are of an even texture and free from specks and water-marks; these specks should be carefully avoided, as they are generally small particles of iron left in the substance of the paper during the process of manufacture, and which, brought in contact with any salt of

silver speedily produces a brown stain on the paper of considerable size. The suitability and quality of the paper is best ascertained by holding each sheet opposite a strong light, either of a window or lamp, and when approved a pencil mark should be made on one side of each sheet for the purpose of distinguishing it when required.

#### PREPARATION OF THE PAPER.

The chemical solutions required for this purpose are two, viz. :—

1. Ten grains of muriate of baryta dissolved in one ounce of distilled water.
2. Solution of ammoniacal nitrate of silver, containing about 50 grains of nitrate of silver in the ounce.

The ammoniacal nitrate of silver, the employment of which was first suggested by Mr. Alfred Smee, is most conveniently prepared in the following manner :—In a two-ounce stopped phial, place 50 grs. of crystallized nitrate of silver, and pour over it one ounce of distilled water. When the crystals are dissolved, some strong solution of ammonia is added, a few drops at a time, and the phial well shaken after each addition. The whole first becomes of a dark brown colour from the formation of a precipitate of oxide of silver, but, immediately the proper quantity of ammonia is added, the oxide of silver is dissolved, and the solution becomes perfectly clear ; it is now ready for use.


There are three equally effective methods of applying these solutions to the surface of the paper, and, as they are applicable to other processes about to be described, I shall, therefore, give the manipulation of each, pointing out any particular circumstance that may indicate the one to be preferred :—

1. A small quantity of the solution to be applied, is poured on to the surface of a horizontal glass plate, or else over the bottom of a flat earthen dish, somewhat larger than the sheets of paper to be prepared. A sheet of the selected paper is then carefully laid on to the solution, the marked side downwards, taking care that no air bubbles remain between the paper and the solution, and also that the back is not wetted ; the paper will be observed to curl upwards from the solution, but this must be prevented by slight pres-

sure over the back of the paper by means of a glass rod or small stick. When the sheet of paper lies perfectly flat and loses its rigidity, at the same time becoming slightly less opaque, it is an indication that the fluid has been sufficiently absorbed. The sheet of paper may then be raised from the solution, allowed to drain for a second or two, and hung up to a cross rail of wood by two pins passed through its upper corners and into the wood. After a minute or so the superfluous fluid accumulates at the bottom edge of the sheet, and is best removed by the application of a piece of thick filtering or plate paper. Any number of sheets of paper may thus be prepared, renewing the solution as required from time to time on the glass plate or dish.

2. The sheet of paper is laid, marked side upwards, upon a wooden board, which ought to be about a quarter of an inch smaller all round than the paper, and a smooth glass rod placed across the left end of the sheet a short distance from its edge, as shown in the following cut:—

Fig. 38.

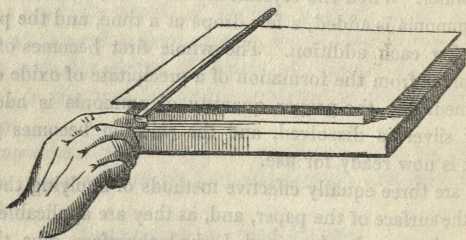

A measured quantity of the solution to be applied is poured in front of the rod, which is then moved to and fro till the solution is equally spread, and the whole surface wetted; after allowing a few seconds for absorption of the liquid the sheet may be hung up, as before described, to dry.

3. The sheet of paper to be prepared is laid on a sheet of bibulous paper, placed on a smooth board, and secured in its position by four pins at the corners. The board is then held in the left hand in a slightly-inclined position, and the solution applied by means of a soft brush, using it in one uniform direction over the



sheet, and removing it as seldom as possible; the extreme edge of the paper must be avoided; but should any of the solution accidentally flow over the edge it will be immediately absorbed by the bibulous paper, and the back of the sheet prevented from being stained. The paper thus wetted is allowed to remain for a few seconds, and then hung up to dry, as before explained. As solutions of silver very rapidly act on ordinary brushes, rendering them unfit for a second application, it will always be found best to employ a kind of extemporaneous brush, invented by Mr. Buckle, made with a piece of glass tube about half inch diameter, and six inches long, into the end of which, by means of a silver wire passing through the tube, and hooked at its extremity, is partially drawn a ball of cotton wool about the size of a walnut; this is dipped into the solution of silver and used as a brush; after being employed for preparing the requisite number of sheets the piece of cotton wool is then thrown away, and replaced by fresh when required.


If the surface of the paper to be prepared be at all greasy, it will be necessary to use a slight amount of friction to cause the solution to wet the surface, in which case the glass rod, or brush, has an advantage over the other method of preparation.

The first operation for preparing the photogenic paper consists in applying to each sheet, on the marked side, the solution of muriate of baryta, by either of the methods detailed, and when dry they will not deteriorate by keeping any length of time. This part of the process may be performed at any time, in the daylight if required, as light has no action on muriate of baryta. When required for use a sheet of this prepared paper is washed over, again on the marked side, with the solution of ammoniacal nitrate of silver, and hung up in a dark room or cupboard to dry; when dry it should be smoothed with a glass rod, and is ready for use, and may be preserved from the light, in a portfolio, or between the leaves of a book, till required to be employed. The time between the final preparation and employment of the paper should not exceed twenty-four hours, as the prepared surface soon begins to darken and spoil.

We have now a surface so prepared that it will very quickly blacken all over if exposed to light; but it will be obvious that if

one part be shaded, and the other exposed, the part covered will remain white, and the whiteness would correspond in outline to that of the body shading it. If a leaf, for example, be placed on a prepared surface of paper, and exposed to the sunlight, the paper will become black all round the leaf, but underneath the blackening effect will be according to the amount of opacity of its various parts, and an impression will be produced corresponding to the various markings of the leaf. It is necessary, however, to obtain a correct copy of the leaf, that it should be in close contact with the prepared surface, so as to prevent any light affecting the paper under the edges of the leaf, and for this purpose is employed a contrivance called a reversing or pressure frame, the simplest form of which is represented in the following cut:—

Fig. 39.



Many forms of this instrument have been devised, but, being all of one principle, they may be described as consisting of one or two pieces of thick plate glass, placed in a wooden frame, with a contrivance at the back, either by a wedge or screws, to press together the two plates, or else a flat board covered with two or three folds of flannel, which can also be pressed against the front glass.

To copy objects that are flat, such as prints, drawings, &c., proceed as follows:—Place a sheet of the photogenic paper on one of the pieces of plate glass, taking care that the prepared side, which is easily distinguished by the mark made for that purpose, is upwards. The print or drawing should then be placed on the paper, printed side downwards, and a small particle of wafer or gum applied at one of the corners, so as to attach it to the prepared paper; the other piece of plate glass is now to be placed so as to press them into close contact. The whole may then be exposed to the light, the drawing to be copied being upwards.

The time required to produce an impression depends, in a great measure, upon the thickness of the paper upon which the print or drawing is made; about ten minutes in a bright sunshine, or half an hour clear daylight, is generally sufficient; but the best method

is gently to slide the upper glass partially off, without disturbing the position of the print or drawing, and, by carefully lifting that part which is uncovered by the glass, see whether the impression is complete; if not sufficiently dark, return the glass to its place, and expose it some time longer to the action of the light, till the copy be sufficiently distinct.

To copy objects that are not flat, such as plants, leaves, butterflies, &c. &c., proceed as follows:—Lay the objects out as desired on one of the plates of glass, and lay carefully over them a sheet of the prepared paper, *very slightly* damped, with the prepared side next to the objects; then substitute for the lower plate of glass the board covered with flannel, and apply a moderate pressure, by which means the objects will be slightly embedded in the sensitive paper, and, after exposure to sunlight, the objects, of course, being towards the light, very beautiful and correct impressions will be obtained.

If the object be very unequal in its thickness at certain points, those parts may, in most cases, be reduced by means of a penknife, without impairing, in the slightest degree, the accuracy or effect of the copy.

There are many ways of modifying the process for obtaining photogenic drawings, from various substances and articles, which cannot fail to occur to the experimenter, and, therefore, need not be particularly described; but although the process may be used for obtaining correct copies of all small objects, either of nature or art, provided they are, or can be, made sufficiently flat, without injury, the objects that will be found best adapted for this purpose are plants, leaves, flowers, ferns, mosses, feathers, wings of insects, prints, drawings, lace, and other similar articles.

#### FIXING THE PHOTOGENIC DRAWING.

When an impression has been obtained by any of the means just described, it is necessary, for its preservation, that the undecomposed salt of silver remaining in the paper be removed.

The best article for this purpose is the salt called hyposulphite of soda, one ounce of which is to be dissolved in one pint of

water. This solution, when about to be used, should be poured into a flat dish of sufficient size to contain the photogenic drawing to be fixed.

After a drawing has been obtained it should be washed in cold plain water for a few minutes, slightly agitating the water while the picture is immersed, to prevent any deposit taking place on its surface. It should then be laid face upward on a flat dish or glass plate, and some hot water poured gently over it, till the whole of the size of the paper appears to be removed; this is known to be the case when the water is quickly absorbed, and the surface becomes free from running liquid on inclining the dish or glass; a fold or two of white blotting paper, which should be free from lines, is then gently pressed on the surface of the drawing. The drawing is now to be laid on the solution of hyposulphite, face upwards, till the whole of its surface appears wetted by the upward absorption of the hyposulphite; it is then to be well washed in separate portions of water till the water comes off tasteless; the picture is now perfectly fixed, and may be dried and exposed to the light without any risk of injury.

The *rationale* of the fixing process is this:—The chloride of silver, which is the result of the preparation of the paper, is very soluble in hyposulphite of soda, whereas the subchloride of silver reduced by the light is not; the consequence is, that, when the photogenic impression is placed in the hyposulphite, all the undecomposed chloride of silver is converted into hyposulphite of silver, which, being very soluble in water, is removed by the subsequent washing.

The hyposulphite of silver having a very sweet taste, which it communicates to a large quantity of water, affords the best criterion for judging when the paper has been sufficiently washed in the fixing process just described.

#### NEGATIVE AND POSITIVE PHOTOGRAPHS.

A photographic impression obtained by the ordinary photogenic paper will, of course, have the light and shades reversed in regard to the original, *i.e.*, the light parts of the original will allow the

light to pass through, and produce shades on the paper, whereas those parts which are thick or opaque, by obstructing the light, will remain white, or nearly so. These kinds of impressions are called *negative* ones, in distinction to those pictures where the lights and shades are as in Nature, when they are called *positive* photographs.

A photogenic copy of a print, for example, will, in the first instance, be a negative one; and in order to obtain a positive picture, or correct copy of the original, it must be reversed. This can be done by exactly the same means as were used for obtaining it in the first instance, only substituting the negative drawing for the print. In this way any number of positive copies may be obtained from one negative picture.

### THE CALOTYPE OR TALBOTYPE.

The word *Calotype* is derived from two Greek words, signifying "beautiful picture or image." The Calotype, or as it is sometimes called Talbotype, process, for taking pictures on paper, has been patented in this country by Mr. Fox Talbot, in whose specification it was first described; it differs, in one respect, from all the former photogenic processes, inasmuch as the image formed on the calotype paper is quite invisible when taken from the camera until washed over with a liquid containing gallic acid, when the picture gradually appears in all its details. In this particular the beautiful process bears a remarkable analogy to the daguerreotype.

To produce a calotype picture there are five distinct processes, all of which, with the exception of the third, viz., exposure in the camera, must be performed by the light of a lamp or candle, surrounded by a yellow glass, or else in a chamber where the whole of the daylight that illuminates it, first passes through a yellow glass, or several thicknesses of yellow calico; they are all very simple, but at the same time all of them require care and attention. The first, and not the least important, is

## IODIZING THE PAPER.

Much depends upon the paper selected for the purpose; it must be of a compact and uniform texture, smooth and transparent, and of not less than medium thickness. The best I have met with is a fine post paper, manufactured expressly for this process, by "R. Turner, Chafford Mill." Having selected a half sheet without flaw or water-mark, and free from even the minutest black specks, the object is to spread over its surface a perfectly uniform coating of the iodide of silver.

This is accomplished either by the mutual decomposition of two salts, nitrate of silver and iodide of potassium, in the substance of the paper, or else by the employment of the double iodide of silver. In the former method the paper is first prepared on one side with a solution of nitrate of silver, made by dissolving 20 grains in an ounce of distilled water, and then allowed to dry in the dark. This application of the nitrate may be made by either of the methods detailed at page 34.

The nitrate of silver spread upon the paper is now to be saturated with iodine, by bringing it in contact with a solution of the iodide of potassium; the iodine goes to the silver and the nitric acid to the potash.

The solution of iodide of potassium is to be of the strength of one ounce to the pint of water, and is to be poured into a flat-bottomed dish in such quantity that its bottom is covered to the depth of an eighth of an inch.

The prepared side of the paper, having been previously marked, is to be brought in contact with the surface of the solution. Holding by an upturned margin, the paper is to be gently drawn along the surface of the liquid until its lower face be thoroughly wetted on every part; it will become plastic, and in that state may be suffered to repose for a few moments in contact with the liquid; it ought not, however, to be exposed in the iodine-dish for more than a minute altogether, as the new compound just formed upon the paper upon further exposure would gradually be redissolved.

The paper is therefore to be removed, and, after dripping, it may be placed upon any clean surface, with the wet side uppermost,

until about half dry, by which time the iodide solution will have thoroughly penetrated the paper, and have found out and saturated every particle of the silver, which it is quite indispensable it should do, as the smallest portion of undecomposed nitrate of silver would become a black stain in a subsequent part of the process.

The paper is now covered with a coating of the iodide of silver; but it is also covered, and indeed saturated, with saltpetre and with the iodide of potassium, both of which it is indispensable should be completely removed. To effect the removal of these salts, it is by no means sufficient to dip the paper in water; neither is it a good plan to wash the paper with any considerable motion, as the iodide of silver, having but little adhesion to it, is apt to be washed off. But the margin of the paper being still upturned, and the unprepared side of it kept dry, it will be found that by setting it afloat on a dish of clean water, and allowing it to remain for five or ten minutes, drawing it gently now and then along the surface, to assist in removing the soluble salts, these will separate by their own gravity, and, the iodide of silver being insoluble in water, nothing will remain upon the paper but a beautifully perfect coating of the kind required.

It is also a good plan, to ascertain if all the superfluous iodide has been removed, to let a drop of the liquid from the surface of the paper, fall into some solution of nitrate of silver; if it produce a precipitate the paper must be washed for some time longer; if no precipitate is produced, it may now be dried; but, while wet, do not on any account touch or disturb the prepared surface with blotting paper, or with anything else. Let it merely be suspended in the air, and, in the absence of a better expedient, it may be pinned across a string by one of its corners. When dry it may be smoothed by pressure. It is now "iodized" and ready for use, and in this state it will keep for any length of time.

To iodize paper by means of the double iodide of silver, which process I always follow, being the most simple, proceed as follows:—Dissolve in an ounce or so of distilled water about 20 grains of nitrate of silver, add to this 20 grains of iodide of potassium dissolved in an ounce of water. A precipitate of yellow iodide of silver is formed, and is to be allowed to settle to the bottom of the

vessel; then drain off the clear supernatant liquid, and wash the precipitate two or three times with warm distilled water, allowing the precipitate to settle each time, before pouring off the liquid. The iodide of silver, being now freed from any soluble nitrate of potass or other impurity, is to have sufficient distilled water poured over it to make up one fluid ounce, and the whole well stirred with a glass rod. Crystals of iodide of potassium are now added by small quantities, or even single crystals at a time, ascertaining that each crystal is dissolved before the addition of another. The solution will gradually become clearer, and at last perfectly bright, forming the double iodide of silver. The application of the double iodide to the paper is best performed by means of the glass rod, as described at page 34; and when the surface of the paper has become nearly dry it is placed in a vessel of plain water, which must be changed five or six times during a period of nearly half an hour, or till the surface of the paper becomes of a lemon-yellow colour, and a drop of the liquid from its surface fails to produce a precipitate in solution of nitrate of silver. It may then be hung up, and when dry may be smoothed by pressure. When preparing a number of sheets, it is best to employ two or more vessels of water, which may be alternately changed, the whole of the sheets being first placed in one of the vessels, and then removed, one by one as required, to the other.

The action of this process is due to the fact, that iodide of silver is soluble in a strong solution of iodide of potassium, forming the double iodide, as it is termed, which, being decomposed on the addition of water, forms a precipitate of iodide of silver in the substance of the paper, at the same time the iodide of potassium is dissolved out by the water.

The iodized paper, prepared by either of the foregoing processes, will keep any length of time; it is not in the least sensitive to light, and should bear exposure to the direct rays of the sun without its colour being affected, otherwise the process has not been properly conducted, and the exposure, far from being injurious to it, seems, on the contrary, to increase its sensitiveness. The second process is that of exciting, or



## PREPARING THE PAPER FOR THE CAMERA.

For this purpose are required the two solutions described by Mr. Fox Talbot, namely, a saturated solution of crystallized gallic acid in cold distilled water, and a solution of the nitrate of silver, of the strength of fifty grains to the ounce of distilled water, to which is added a drachm and a half of glacial acetic acid. The solution of gallic acid is made by placing four or five grains of the crystallized acid in a phial, and pouring over it about an ounce of distilled water: the phial and contents are then well shaken for a few seconds, and the solution poured upon a filter (see page 25); the clear liquid that comes through will be a saturated solution of the acid, and if slightly heated, by placing the bottle containing it for a few minutes in some boiling water, it will keep good for a considerable time. When these solutions are about to be applied to the iodized paper, three drops of each should be added to two drachms of distilled water, and the mixture, which is now termed gallo-nitrate of silver, is to be poured upon a clean and level slab of plate glass, diffusing it over the surface to a size corresponding to that of the paper. The prepared side of the sheet of iodized paper is to be applied to the liquid upon the slab, and brought in contact with it, by passing the fingers gently over the back of the paper, so as to exclude any air bubbles, taking care that it is not soiled by the solution. As soon as the iodized paper is wetted with the gallo-nitrate, which is known by its ceasing to curl up, it must be removed and the excess of the gallo-nitrate absorbed by a sheet of fine white blotting paper free from watermark, laid over its surface, and very lightly pressed; it may now be placed, while still damp, in the camera frame between the plate glasses ready for use, by which it is protected as much as possible from the action of the atmosphere. If properly prepared it will keep perfectly well for four and twenty hours at least, preserving all its whiteness and sensibility.

If the paper is required of its utmost degree of sensitiveness, as for portraits, the quantity of water employed to dilute the gallo-nitrate may be greatly reduced, even to a few drops, in which case the whole of the process must be quickly and skilfully performed, as it rapidly decomposes, and will not keep longer than two or three

minutes. The degree of dilution must in a great measure depend upon the judgment of the operator, and should be proportioned to the brightness of the day, or brilliancy of the object, the foregoing proportions being the best average strength that can be given. The third process is that of

### THE EXPOSURE IN THE CAMERA,

for which, as the operator must be guided by his own judgment, few directions can be given, and few are required, as the peculiar manipulation for each form of camera has been before described. He must choose or design his own subject, he must determine upon the aperture to be used, and judge of the time required, which will vary from a few seconds to eight or ten minutes. The subject ought, if possible, to have a strong and decided effect; but extreme lights, or light-coloured bodies in masses, are by all means to be avoided. When the paper is taken from the camera slide, very little, or more commonly no trace whatever, of a picture is visible until it has been subjected to the fourth process, which is

### BRINGING OUT THE PICTURE.

This operation should be performed with the like amount of care that was required to prepare it for the camera, both as respects the perfect cleanness of all the vessels employed, either for mixing or applying the chemical solutions, and the avoiding all excess of light, beyond what is required for convenient manipulation.

The solutions required for bringing out the latent picture, are the same as those employed for preparing the paper, viz., solution of gallic acid, and aceto-nitrate of silver. These solutions should be mixed in equal proportions, say half a drachm of each, to which add half a drachm of distilled water. This mixture is to be applied to that surface of the paper on which the latent image is formed by either of the methods before described, taking care that the whole of the surface be thoroughly wetted; it is then laid, face upwards, on a plate of glass or other clean substance, and the picture will be observed to gradually appear in all its details. During the de-

velopment of the picture, it is necessary to keep the surface wet, otherwise the light parts of the picture sink, and become opaque; this is done by applying, when necessary, a fresh quantity of the mixture of gallic acid and aceto-nitrate of silver. If the picture is very tardy in making its appearance, which will generally be the case in cold weather, it can be much accelerated by the cautious application of heat, and a better result by this means obtained than would otherwise be produced. The best method of applying heat is by holding the picture over the steam from some hot water, placed at the bottom of rather a deep dish.

If any part of the picture, although wet with the "gallo-nitrate," should begin to stain, and give indications of the appearance of dark waves, before the whole is sufficiently developed, it will be found the best plan instantly to remove the whole of the excess of the "gallo-nitrate" from its surface; this is done by placing the picture, face upwards, upon a piece of clean blotting paper placed on a smooth board or glass plate, and then by a smooth glass rod lightly pressed on one end of the picture, and moved briskly to the other, the whole or greater portion of the decomposing gallo-nitrate will be removed. A quantity of the solution of gallic acid alone, is now to be poured over the surface of the picture, which will enable it to become sufficiently developed without the formation of any stains.

When the picture is sufficiently clear and defined, it will require to be immediately subjected to the next operation, which is—

#### FIXING THE PICTURE.

The object in this process being to remove the excess of nitrate of silver, and also of the yellow iodide of silver, it will be found advisable in the first instance to place the picture, or photograph, as it may now be termed, face downwards, in a vessel of clean water, which must be changed three or four times during a period of eight or ten minutes, the photograph during that time being kept in slight motion and prevented from settling at the bottom of the vessel; it may now be removed and pressed between some folds of clean white blotting paper, which, as before mentioned, for all pho-

tographic purposes, must be free from lines and watermarks. The greater portion of nitrate of silver being removed by the washing, the remainder, together with the iodide of silver, is to be dissolved out by placing the photograph in a warm and strong solution of hyposulphite of soda, containing about four ounces to the pint of water; it may remain in this solution for a few minutes, or till the yellow colour of the iodide disappears, after which it must be washed in a considerable quantity of common water, and finally, to ensure the whole of the hyposulphite of silver being removed from the paper, may be suffered to remain for a few hours in a fresh quantity of water; on removal from which, and drying between folds of blotting paper, it will be found perfectly fixed, and will undergo no further change when exposed to the light.

The photograph thus obtained is a *negative* picture, *i.e.*, the positions of the objects, together with all the lights and shades, are reversed in respect to their natural appearance, and, although its production may appear somewhat tedious, it will be found by no means difficult. If the chemical agents be perfectly pure, the apparatus properly constructed, the *intention* of each separate process kept in view, and the manipulation recommended correctly followed, the operator may rely with confidence on a satisfactory result.

### THE PRINTING PROCESS.

The negative photograph obtained by the process described in the preceding pages is capable of yielding a vast number of beautiful impressions, in which the relative positions and perspective of the various objects, and their lights and shades, will be correct as in nature. There are many methods of obtaining these impressions as regards the prepared paper employed; the best process with which I am acquainted is precisely that described at page 35 for photogenic drawing. The best method of preparing the negative photograph is to lightly burnish the surface on which the picture is impressed by means of a steel or agate burnisher; the photograph is laid on a smooth glass plate, and the burnisher applied to various parts of its surface till the whole assumes an equally polished and smooth appearance. By this operation the parts of the paper rendered woolly by the various washings, &c., are pressed together and

made more pervious to the rays of light, and some fine portions of detail are brought out and rendered capable of being produced in the printing, in consequence of the surfaces being brought into close contact.

It sometimes happens that the light parts of the negative are not sufficiently transparent to yield good impressions, in which case they can be improved by scraping a small quantity of white wax over the surface of the picture; a sheet or two of blotting paper being then laid over the wax and a hot flat iron passed a few times over the blotting paper, the wax becomes absorbed and the picture rendered more permeable to light.

The sheet of paper prepared with the muriate of baryta and nitrate of silver, and upon which the positive impression is to be made, should be perfectly flat and smooth; upon this is laid, face downwards, the negative photograph, placing a particle of wafer at one or more of the corners, and, the whole being placed in the reversing frame, is exposed to the light. The printing process should be allowed to proceed some time longer than the shade of tint would lead the operator to suppose, as the tint of colour is slightly lightened by the subsequent fixing process; at the same time it should not be carried so far as to injure the lights of the picture. The details of the printing process, and also of the method of fixing the photographs, having been fully described before at page 35, need not be repeated here.

When the photograph is finished it should be preserved from all damp and dust, and kept in the light, otherwise it is apt to slightly fade. This can conveniently be done by giving it a coating of gelatine over its surface, or mounted in the usual way with a glass in front.

## DAGUERRETYPE.

The daguerreotype is a process by which correct copies of objects can be made from nature on polished surfaces of silver. It derives its appellation from its inventor, M. Daguerre, an ingenious French

artist, who published the process in August, 1839, for which he, together with M. Niepce, who assisted him in his investigations, received the grant of an annuity from the French Government.

The process has been patented in England by Mr. Berry, in 1839, and in his specification is called "A new and improved method of obtaining the spontaneous reproductions of all the images received in the focus of the Camera Obscura;" since which time it has been greatly improved, and still is improving in many particulars, especially as regards its simplicity and quickness of action.

### DESCRIPTION OF THE PROCESS.

Daguerreotype pictures, as they are called, are taken on copper plates, covered with a coating of silver, which should be as pure as possible, and of sufficient thickness to allow of its being very finely polished. A superior description of Sheffield plate is the kind generally used, which, after being cut to the sizes required, is flattened or planished by the hammer, and afterwards polished on a lathe to the required surface. These plates, properly prepared and cut to any size, can be obtained ready for use.

There are several varieties of these plates under the names of English and French plates, manufactured, as the names import, in those countries. The plates manufactured in England are generally thicker and have more silver on them than the foreign, from which circumstance they can receive a finer surface, and are more applicable for beginners, as they will bear being cleaned for a great number of times. The French plates being cheaper than the English can be employed when practice has enabled the operator to be nearly certain of his results; they are usually marked 1.40 and 1.30, indicating the quantity of silver on them, and consequently their quality: those marked 1.40 will scarcely admit of being used a second time, but the other may, perhaps, with care be polished three or four times without removing the silver.

The method of proceeding consists of six distinct operations, viz. :—

1. Cleaning the silvered plate.
2. Rendering its surface sensitive to light, by exposing it to the vapour of iodine, bromine, or their combinations with chlorine, &c.

3. Exposing the prepared sensitive plate to the focus of either a refracting or reflecting camera.
4. Bringing out the picture by exposing it to the vapour of mercury.
5. Removing the sensitive surface of the plate which has not been acted upon by the light.
6. Fixing the picture by giving it a coating of gold, and drying.

#### CLEANING THE SILVERED PLATE.

The object in this operation is to obtain a perfectly pure and polished surface of silver; it is therefore of the greatest importance that the articles used in the latter part of the process should be perfectly free from grease or any other article of a fixed oily nature. Many ways and substances have been proposed for these purposes; but the following methods I have generally found produce the best results, and are most simple in their details. The materials required are calcined tripoli, prepared lampblack, rouge, and olive oil.

The calcined tripoli should be in a state of an impalpable powder, and perfectly free from any large particles, which would cause scratches on the plate; it is best kept for use in a metal or wooden box, contrived expressly for this purpose, the open end of which is closed by a piece of fine muslin tied over it, and the whole covered with a lid to protect it from the dust.

The lampblack should be prepared by making it red hot in a crucible till vapours cease to arise from it; the crucible may then be removed from the fire, closely covered up, and allowed to cool. The lampblack thus burnt should be reduced to a fine powder in a glass or porcelain mortar, and the portion required for use kept in a similar box to that employed for the tripoli.


The rouge should be the finest washed that can be obtained, and may be kept in a similar box to the other materials.

The first process, which is that usually adopted at the photographic establishments where large quantities of plates are wanted for use, requires a lathe, to the head of which can be adapted, by means of the proper screws, a series of circular buffs, the usual number being three. These buffs consist of circular discs of

wood, one side of which is covered with a fold or two of unbleached cotton velvet. The buff N. 01 is prepared with olive oil and tripoli; No. 2 with tripoli alone; and No. 3 with lampblack and a small quantity of rouge, or lampblack alone. The plate to be polished is placed in a shallow cavity on the surface of a flat piece of metal, having a projecting tube at its back, and into which is placed a circular iron rod mounted with a wooden handle, for the purpose of pressing this metal holder and its contained plate against the circular buff.

The method of proceeding is as follows:—Screw on the buff No. 1, adding, if necessary, some fresh tripoli and oil, and place the lathe-rest about three inches from its surface; the plate is now pressed lightly against the buff, a short distance from its centre, supporting the iron pivot against the rest. The lathe being put in motion by the foot causes the plate to revolve very rapidly over the buff, and very quickly removes from it any former picture, scratch, or tarnish. The plate and its holder should now be lightly wiped with a portion of cotton wool to remove as much as possible of the superfluous oil, &c. The buff No. 2 is now to be substituted for the oil buff, and the plate again applied in the way just described till all appearance of oil is removed, and the plate appears equally polished. The plate is now laid, silver side upwards, on a stand similar to the one here represented,

Fig. 40.




and the flame of a spirit lamp applied underneath till a slight smoke appears to rise from it, and its surface assumes a slight white tint; by this process the remaining traces of oil are burnt away, and the plate is ready to receive its final polish by means of the buff No. 3.



When the plate is properly polished its surface should look quite black and free from scratches when viewed in a particular light. If this is not the case, it must be applied some time longer to the buff No. 3 till that result is produced.

The other method of polishing where a lathe cannot be obtained, or would not be admissible on account of its cumbrous nature, consists in employing a series of cotton velvet buffs, varying in size from 3 inches by 12 inches, to 9 inches by 18, according to the size of the plates. The least number required is four; the first buff is prepared with tripoli and oil; the second and third with tripoli alone; and the fourth with prepared lampblack and a very small quantity of rouge; they must be kept separate from each other, and each carefully reserved for its own particular use. The method of proceeding is to lay the plate face downwards upon the oil buff No. 1, and then, by means of a similar plate-holder to that employed for the lathe, or else one made of wood of the form represented on the cut, the plane surface of which is rendered adhesive by some prepared indiarubber, the plate is briskly moved over its surface with a very slight pressure for the space of a minute or so; it is then cleared from adhering oil, &c., with some cotton wool, and rubbed lightly first on No. 2 buff, and afterwards on No. 3, adding some fresh dry tripoli as required.

Fig. 41.



The plate is now heated with a spirit-lamp, and as before described, finished on the buff No. 4.


If the plate to be polished be very free from scratches, and has not been subjected to the setting process with salt of gold, the use of the oil buff may be dispensed with, and those prepared with tripoli and lampblack alone used.

The following are the most important precautions to be observed to insure the proper result in the foregoing processes. The buffs and polishing materials should be carefully preserved from dust

dirt, and damp; the former of these is easily accomplished by keeping each separate buff in its own case, which may be made either of wood or parchment, and the latter by keeping them in some dry place. If there should be any doubt relative to the buffs being perfectly dry, it will be advisable to place them, well protected from dust, before a fire, a short time previous to using.

When the plate is polished by either of the processes described, it may be protected from injury in a wooden or metal box, similar to the one represented in the cut.

Fig. 42.

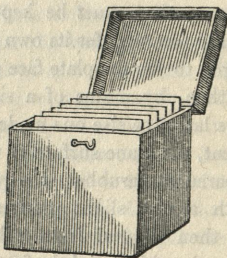

When the plate is about to be used it should receive a final polish, and have its grain laid, as it is termed, in a particular direction, by means of a buff either covered with cotton velvet, or, what is preferable, a piece of smooth, soft doe-skin, of the shape here represented.

Fig. 43.



The plate of a small one can be supported on the ends of the fingers of the left hand, using the buff with the right; if the plate be too large or thin to be supported on the fingers, any convenient form of plate-holder can be employed, taking care that it is perfectly free from dust or grease. The buff should be briskly rubbed over the plate with a slight degree of pressure for a few seconds, or till all the fine lines on the surface of the plate appear in one uni-

form direction, bearing in mind that for portraits the lines should not be in the direction of the face, but across it; and for views, in the direction of the view.


The plate is now ready, and should immediately be subjected to the next operation, which is

#### APPLYING THE SENSITIVE COATING.

The simplest form of apparatus necessary for this purpose consists of two porcelain or glass pans, ground on the edges and furnished with plate-glass covers, and a series of wooden or metal frames of the size of the plate to be prepared: one of these pans is for holding the iodine, and the other the accelerating material. The plate to be prepared is placed in its proper frame, and substituted for the plate-glass cover of either pan, as may be required; the progress of the preparation being observed from time to time by the tint of colour produced on the plate when removed for an instant and viewed at such an angle that the light transmitted through a sheet of white paper held before the plate may be reflected to the eye. When the proper colour is obtained the plate is exposed for an instant or two longer to remove any effect of the light and then rapidly placed in the camera frame: the glass cover is now replaced.

In consequence of being obliged to remove the cover of these pans to observe the colour of the plate, the vapour of iodine, &c., within the pan becomes disturbed, and rarely produces an even coating: this is avoided by using the glass pans of greater depth, and mounted as shown in the accompanying cut:—

Fig. 44.

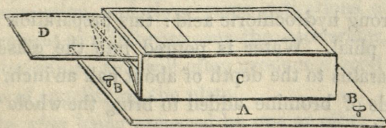


The plate to be prepared is placed in the proper opening at the top of the box, and on removing the glass sliding-cover at

placing it again before the plate is removed a much better result is obtained.

The only form of apparatus that can be relied upon for producing an uniform good result is that shown in the cut, or one constructed on similar principles.

Fig. 45.

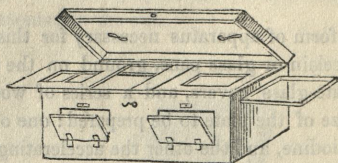

It is technically termed a bromine apparatus, and consists of two deep glass pans with polished sides, and mounted in a wooden box, at the back of which are two openings, corresponding to the two pans over which is fastened a piece of white paper. In the front of the box and immediately opposite the back openings are two small doors opening outwards, and each lined with a piece of looking-glass. Two glass covers and a series of wooden frames sliding over them on the top of the box complete the apparatus. From half to one ounce of pure crystallized iodine is placed at the bottom of one of the pans and the accelerating material in the other, and they are then closed with their respective covers, and the whole apparatus placed before a window with a moderate light.

The accelerating material which I have uniformly found produce the best and most certain results is a chloride of bromine, made by mixing one ounce of a saturated solution of bromine with one drachm of strong hydrochloric acid: this preparation must be kept in a stopped phial. Water is poured into the glass pan of the bromine apparatus to the depth of about half an inch, and sufficient of the chloride of bromine added to bring the whole to the colour of very pale sherry.

The plate to be rendered sensitive to light is placed in its required frame at the top of the bromine apparatus and immediately

over the pan containing the iodine; the plate-glass cover is then removed so as to expose the plate to the vapour of the iodine below; the small mirror is now so adjusted that by looking into it the white paper at the back can be seen reflected from the surface of the silver plate and any change of colour immediately perceived. When the plate has assumed a light straw colour the cover is to be returned over the iodine, and the slide holding the plate shifted over the pan containing the chloride of bromine; the cover is now to be withdrawn, the mirror adjusted as for the iodine; and the glass cover being removed, the plate is exposed to the vapour till it becomes of a deep yellow colour, when it is returned over the iodine till of a rose tint, and immediately placed in the camera frame. The dilute solution of chloride of bromine will serve to prepare a considerable number of plates; and when it fails to produce its effect it will always be found the better plan to mix a fresh quantity rather than increasing its strength by the addition of more of the strong solution.

There are a great many preparations of bromine known by the names of eau bromée, bromide of iodine, Hungarian solution, Woolcott's American accelerator, bromide of lime, &c., which are employed by some operators with much success.

When the bromide of iodine, or Hungarian solution, is employed, they should be diluted with four or five times their bulk of water, and the plate, previously iodined to a deep yellow, exposed to them till of a deep rose or violet colour. Woolcott's accelerator and bromide, of lime both require the same tints as the chloride of bromine before described. The bromide of lime, chloro-bromide of lime, and other dry accelerators of that character, are used in the bromine apparatus, spread evenly over the bottom of one of the pans to the depth of about a quarter of an inch.

Should the plate by accident be left too long over the iodine in the first preparation, and show some indications of a rose tint, it must be brought to a full rose over the accelerator, and then to a blue over the iodine; this will often produce a good result, and save the trouble of repolishing the plate.

The plate, after being prepared by one or other of the foregoing processes, must be returned to the dark box or camera back till required for the next process, viz. :—

## EXPOSURE IN THE CAMERA.

The mode in which this is effected must, of course, depend upon the construction of the camera, whether it have a lens, as originally proposed by Daguerre, or a concave mirror or speculum, which is the apparatus patented in this country by Mr. Beard. Both kinds have their advantages. The refracting camera, as recently improved, appears to possess all the capabilities without many of those inconveniences which attend on the manipulation with the reflecting camera, and, being withal less expensive, is now the form generally used.

The first thing to be attended to, before introducing the plate, is to place the camera on some firm support, and opposite to the object wished to be copied; after which the focus should be adjusted with the greatest care till a perfectly clear and distinct image of the object is seen on the piece of ground-glass, which should be placed in exactly the same position as the plate is to occupy, taking especial care that the ground side of the glass should correspond to the prepared surface of the plate. When the focus is obtained, the light should be shut off by a brass cap or other contrivance for that purpose till the plate is introduced, or the camera may be taken into a dark room, and have the plate put into its place, when it can be brought into the light, having, of course, made those obvious arrangements that the object and the camera be placed in precisely the same relative positions they occupied when the focus was adjusted.


The camera may then be opened to allow the light to fall on the plate through the lens. The time requisite for it to remain open will depend, in a great measure, upon the season of the year, time of the day, and the brightness or clearness of the atmosphere. The time usually required with a good achromatic and a well constructed camera varies from one to sixty seconds.

When the camera has been opened a sufficient time, which can only be determined by observation and experiment, close the front aperture, and take it into a dark room, when the picture, which is impressed on the sensitive surface of the plate, is to be made visible by being exposed to the fumes of mercury.

## MERCURIALIZING THE PLATE.

The apparatus required for this operation is called a mercury box, and is shown in the accompanying cut:—

Fig. 46.



The body, A, is made of wood, and has an iron cup fixed in the bottom for holding the mercury, which is heated by a spirit lamp, F; the upper part of the box, A, is grooved, so as to receive the same sliding frame, B, that fits the back of the camera, and holds the prepared plate, or else the prepared plate alone; at the front of the box is a small yellow glass window, C, over which slides a shutter, D. When about to be used, pour a small quantity of pure mercury (four to six ounces) into the metal cup at the bottom of the box; the mercury should then be heated by means of a spirit lamp, till the outside of the metal cup can be touched with the finger without much inconvenience. The plate may then be taken from the camera and placed in the mercury-box; and, after a short time, by cautiously applying a lighted paper to the side, and looking through the glass in front, the development of the picture can easily be perceived.

If the mercury be made very hot, the picture soon makes its appearance; but, generally speaking, when done too rapidly, the minor details are lost, and the plate is apt to become spotty; it is always advisable, where time is not a great object, to do the operation rather slowly than otherwise, as a much clearer and sharper outline of the picture will be obtained by this means than if done rapidly. The usual time required is from five to twenty minutes.

If the mercury box be furnished with a thermometer, which is sometimes the case, the temperature may be kept about 90°.

The mercury should be perfectly dry and free from any particle of oxide, and should be poured into a bottle after each series of experiments. When it loses its brilliancy, it may be purified by filtering through a paper cone, having a very fine opening at the bottom. The mercury-box ought also to be carefully dusted out before using.

When the picture has become sufficiently distinct, it should be removed from the mercury box, and subjected to the next operation, viz :—

#### REMOVING THE SENSITIVE COATING.

The solution required for this purpose is made by dissolving two ounces of hyposulphite of soda in one pint of water; this solution will serve many times if it be filtered before using. The solution is placed in some convenient shallow vessel, and the plate quickly immersed in it; the colour will be observed to gradually disappear, and when that is the case it should be placed in a vessel of filtered water, to remove the excess of hyposulphite, and subsequently a small quantity of distilled water poured over its surface.

#### FIXING THE PICTURE.

The solution of gold which is required for this process is prepared by dissolving 15 grs. of chloride of gold in one pint of water, and adding it little by little to a mixture of 60 grs. of hyposulphite of soda and eight ounces of water, the whole being well agitated between each addition. The solution, at first slightly yellow, becomes afterwards perfectly limpid; and the solution of gold being poured over its surface until it is perfectly covered, and the flame of a large spirit lamp applied to the under surface, moving it gently backwards and forwards, that every part may be equally heated, the picture will be seen to brighten, and become in a minute or two of great force. When this effect is produced, the liquid should be thrown off, and the plate instantly dipped into water, washed, and dried. If the plate be a large one, it is most conveniently dried by placing it on a smooth and clean piece of cop-



per or tin plate, and some boiling distilled water poured over its surface, at the same time inclining the plate so that the water may run off from one of its lower corners, and it will in a very short time become perfectly dry. Before the surface of the plate becomes dry it is to be placed, face upwards, upon the fixing stand, which is so constructed as to preserve it in a perfectly horizontal position by means of levelling screws.

If the plate be of a small size, it can be conveniently dried over a spirit lamp. It should be held, by means of a small pair of pliers, by one of its corners; and some filtered distilled water poured over its surface; by inclining the corner held by the pliers, the greater portion of the liquid will flow to that part, and can be removed by touching it with a piece of rag or blotting paper; the spirit lamp may then be applied to the upper corner of the plate till it begins to dry, and the flame gradually brought lower down, till the whole surface is finished. Gently blowing downwards on the plate will expedite the process, as well as prevent, in a great measure, the formation of spots.

It sometimes happens that, while the plate is being heated with the solution of gold, a film of silver detaches itself and swims in the liquid, of course destroying part of the picture. This accident is probably owing to the oxidation of the silver while under the influence of too much heat.

The lamp should be removed as soon as small bubbles of air appear to form on the surface of the metal. When the picture is not perfectly fixed, it is better to make a second trial, rather than run the risk of spoiling a good picture by trying to fix it perfectly the first time.

#### COLOURING DAGUERREOTYPES.

As objects copied by the daguerreotype process are only represented in light and shade, not in the colours as they appear in nature, it has been suggested, after the picture has been set, to colour them by hand, similar to a painting, and certainly, when done in an artistic skilful manner, it produces a very pleasing effect. The simplest method is to use dry colours, ground extremely fine, with some dry gum or starch. The picture must be well set with gold, and the colour applied or dusted on with a fine

camel's-hair pencil, taking up a very small quantity of colour at a time, removing the superfluous colour by blowing it off with a caoutchouc bottle; when the desired tint is produced, breathing on the plate will cause the colour to adhere. Mr. Claudet's method is to mix a small quantity of the colour with spirit of wine, applying it to the plate with a camel's-hair pencil, and if not sufficiently dark, some of the dry colour is applied over it, to which it will adhere. As a general rule, the colours should be applied very cautiously, as it is very difficult to remove them when once on the plate. The best colours to be used are carmine, chrome yellow, and ultra-marine, by combining which any desired tint may be obtained.

#### ELECTRO-SILVERING DAGUERRETYPE PLATES.

A perfectly pure surface of silver can be precipitated by the agency of a galvanic battery on an ordinary daguerreotype plate, and by some operators is thought to add much to the brilliancy of the proofs subsequently obtained on such plates. The apparatus necessary consists of a Smee's battery and glass depositing cell; the battery is charged with a mixture of one part of sulphuric acid and seven or eight parts of water, and the depositing cell with argento cyanide of potassium, made by dissolving two drachms of the oxide of silver in a mixture of one ounce of cyanide of potassium and eight ounces of water. A piece of silver foil, about the size of the daguerreotype plate, is to be placed in the depositing cell, and attached by means of a silver or copper wire to the silver plate of the battery; a similar wire having a small binding screw at one end, is fastened to the zinc of the battery, and the plate to be silvered is fixed on the small binding screw. The daguerreotype plate, which must be perfectly clean and free from grease, is now immersed in the depositing cell, immediately opposite to, and about half an inch from, the silver foil; in about eight or ten seconds a sufficient coating of silver will be deposited, when the plate may be removed and well washed in plain water, and after drying with a small quantity of cotton wool and tripoli, it may be polished with the lampblack buff, and is ready to be iodized, &c. as an ordinary plate.

## PHOTOGRAPHY ON GLASS.

In consequence of the perfect transparency and evenness of glass plates, which render them particularly adapted for photographic purposes, many processes have from time to time been devised for rendering them available, by spreading films of various substances, such as albumen, gelatine, serum, starch, collodion, &c., which are then rendered sensitive to light by being impregnated with iodine and various salts of silver. The best processes with which I am acquainted are those in which albumen or collodion are employed to produce the necessary film To obtain

## COLLODION PICTURES

I cannot give better directions than those given by Mr. F. Horne to Robert Hunt, Esq., and published in the "Art Journal" of July, 1851 :—

"The PREPARED COLLODION (a solution of gun-cotton in ether) contains a small quantity of iodide of silver, previously dissolved in iodide of potassium, and should be sufficiently limpid to run freely over a plate of glass, when poured upon it. If the collodion be too thick, great difficulty will be experienced in obtaining an even coating; but, where of a proper consistency, plates of any size may be coated. Ether being the solvent in the collodion, by adding additional quantities any degree of thinness may be obtained.

"The plan of coating the plates is as follows :—Take a piece of flat glass cut to the size of your frame, and, having washed it with water, and wiped it quite dry, hold it at one corner, or, if large, place it on a levelling stand, and pour on the centre of it a good body of the collodion, prepared as described, which will readily diffuse itself equally over the surface. Immediately pour the liquid off again into a bottle from one corner, and by bringing the hand holding the plate down a little, that the liquid may run to the lower edge, and drawing the mouth of the bottle along, those lines

first formed will run one into the other, and give a flat, even surface. Very little practice will soon enable any operator to obtain this result. The plate is now immediately, and before the whole of the ether has had time to evaporate, to be immersed in a bath of nitrate of silver, 30 grains to the ounce of distilled water, until the greasy appearance which it first presents on immersion is entirely gone, and the silver solution runs very freely over the surface. The plate should now, in its moist state, be placed in the camera, and the picture taken, the time of exposure varying of course with the light; but for a portrait, and with a moderately quick lens, from three to thirty seconds will be sufficient. P. W. Fry, Esq., who was the first to practise with the collodion, has obtained beautiful portraits by placing the sitter in the open air in the shade, and simply removing the cap from the lens, and closing it again as soon as possible. The agent for developing these pictures is the pyro-gallic acid, as recommended by Mr. Archer. The solution of pyro-gallic acid should be made as follows:—Pyro-gallic acid, 3 grains; glacial acetic acid, 1 drachm; distilled water, 1 ounce. After exposing the plate in the camera, it is to be placed face upwards upon a levelling stand, and a sufficient quantity of the above solution should be poured equally and quickly over the surface, and the picture allowed to develope, occasionally slightly moving the plate to prevent any deposit from settling at one spot. A few drops of a solution of nitrate of silver, five grains to the ounce, may also in dull weather be added to the pyro-gallic with advantage just before pouring it over the plate; but in very bright weather the picture will develope sufficiently quick with the pyro-gallic solution alone. The progress of developing may be readily judged of by holding a piece of white paper occasionally under the plate, and as soon as sufficient intensity has been obtained, the solution must be poured off, and the plate washed by a gentle stream of water. After this, the surface should be covered with a saturated solution of hypo-sulphite of soda, which will almost immediately remove the undecomposed iodide, and fix the picture; and another stream of water must then again be poured over to free the plate from hypo-sulphite, and the picture is finished.

“In this state they are more or less negative by transmitted light: but the most beautiful and decided positives may be ob-

tained by the simple addition to the pyro-gallic solution of a small quantity of nitric acid, care being taken not to add too much. I have also obtained purple and green pictures, the former by using acetate of lead, and the latter with acetate of lime and ordinary gallic acid.

“The pictures thus obtained may be treated as negative pictures, and printed from by any of the methods employed to obtain positives from paper negatives.”

The glass plates employed should be of thin plate glass, cut to the size of the camera frame, and slightly ground on their edges. The bath to contain the solution of nitrate of silver may be formed either of glass, porcelain, or gutta percha, care being taken that the solution of silver is kept perfectly free from dust. It will serve for a great number of pictures, and will only require to be renewed should it, by accident, get the smallest quantity of hypo-sulphite of soda in it, or else fail to produce an even film of iodide, when the plate is immersed.

Various modifications of the foregoing process have been recommended for increasing its sensitiveness, such as the addition of arsenious acid, &c., and developing the picture with the proto-salts of iron; but, although excellent pictures can be obtained by these processes, they do not appear to possess any advantage over Mr. Archer's process, which will give most beautiful results under favourable circumstances in less than one second, and with all the depth of tone than can be desired.

The colodion process is most particularly adapted for portraits which can generally be taken immediately the plate is prepared, and before it has time to dry. It is not so applicable for views, unless taken under the same circumstances as portraits, in consequence of the plate losing all its sensitiveness immediately it is dry.

Very beautiful positive pictures are produced, if the solution of pyro-gallic and acetic acids, of the strength before indicated, be diluted with an equal bulk of distilled water, and a small quantity of strong nitric acid added, equal to the proportion of about three drops to two drachms of the diluted pyro-gallic acid. When the picture is set with the hypo-sulphite, washed, and dried, it can be protected from injury, and its effect greatly improved, by pouring

over its surface some mastic varnish, diluted with camphine, and coating the other side with same black japan varnish.

There are several methods of preparing the collodion, but the best with which I am acquainted is a slight modification of one described by M. Levonius:—Half an ounce of dried nitrate of potass in fine powder is to be mixed with three-fourths of an ounce of ordinary strong sulphuric acid of sp. gravity, about 1.850, in a porcelain capsule, with a glass rod, and half a drachm of clean dry cotton is then added as quickly as possible, and stirred about in the mixture for about five minutes; when removed, it is to be carefully and thoroughly washed with water, and dried by exposure to a warm atmosphere. Ten grains of the gun cotton thus obtained is dissolved in half an ounce of sulphuric ether, to which is added one drachm of alcohol. Five grains of iodide of potassium is now dissolved in the smallest quantity of water, and added to the collodion, together with about three ounces of sulphuric ether so as to enable it freely to flow over a glass plate.

For obtaining views and representations of fixed objects, where time is not of so great importance, and it is absolutely necessary to employ a dry plate, the employment of albuminized glass plates will be found preferable to those prepared with collodion. The process with

#### ALBUMINIZED GLASS PLATES

is conducted in the following manner:—To the white of one egg, from which the white cords should be carefully removed, add ten drops of a saturated solution of iodide of potassium, and about two drachms of water, the whole should be well beaten up to a white froth, and placed in a convenient vessel for six or eight hours, at which time it will have become a clear solution. The glass plate is to be cleaned with great care, by the employment of a small quantity of caustic alkali and abundance of water, drying it perfectly, first with a piece of linen cloth, and subsequently with a portion of old silk. The plate is supported on the tips of the fingers of the left hand, and the clear albumen poured over in considerable quantity, till the whole of its surface is wetted; the superfluous albumen is now poured off at one of the corners, and

the lower part of the plate wiped with a cloth two or three times, which, by removing a portion of the excess which there takes place, tends to equalise the coating.

The plate is now to be placed in an atmosphere of steam, as recommended by Mr. Reeves, and which is conveniently done by placing it in a square tin vessel containing a little water, and placed over a lamp; in about two minutes the plate may be removed, and the coating perfectly dried by placing it outside the tin vessel till the film becomes transparent. The plate is rendered sensitive by dipping it at one movement into a bath composed of 60 grs. of nitrate of silver to the ounce of water, and 10 drops of glacial acetic acid; this solution after once being used becomes brown, but this change does not impair its action. The plate may remain in the bath for about a second, then drain off the excess of silver, and pass it, face upwards, two or three times through some distilled water; it may be allowed to dry in the atmosphere, protected from dust, and when dry will keep well for 36 hours.

The time of exposure in the camera with the objects illuminated with the sun will vary from ten minutes to half an hour, according to the size, &c. of the lens.

To develop the picture, employ a saturated solution of gallic acid, which may be applied to the surface with a piece of cotton wool; a Buckle's brush answers admirably, and when the detail of the picture is well up, which is usually the case in about half an hour, apply some gallo nitrate of silver of the full strength employed for the calotype process; the detail of the picture will now become more decided and dark, and, when fully developed, apply in a similar manner some solution of hyposulphite of soda, containing about 40 grs. to the ounce of water. Let this remain for a minute or so, and then pour over it very carefully eight or ten ounces of water; allow it to drain and become dry in a close box, or otherwise well protected from dust, and the negative picture is finished. The printing or copying process for the production of the positive picture is precisely that employed for the collodion, and already described at page 35.


### PORTRAITS, VIEWS, &c.

*Portraits.*—To obtain good portraits it is necessary that the time required for the sitter to remain perfectly still should be as short as possible, consequently the apparatus should be of the best construction, and the sitter placed in as light a situation as possible. The open air is the best position. In bright sunshine it is essential, and indeed generally it will be found desirable, to place a canopy of some light blue material over the sitter, so that its shadow may fall beyond the feet, and thus prevent the direct rays of the sun, which ought always to be avoided. If the portrait is taken in a room, the sitter should be placed before the open door or window, so that the features may be strongly illuminated. The sitter should assume an easy natural position, bringing all the parts of the body as near as possible to one plane; that is, the feet and hands should be kept as near a line with the face as possible, for if they project much beyond they will become enlarged and distorted by the camera, especially if it be of short focus. The same precaution must be observed with respect to all objects, such as vases, &c., that are wished to be introduced into the picture.

During the time requisite to remain perfectly quiet, when the camera is opened, the head should not alter its position.

A very convenient method of steadying the head consists in attaching a support at the back of a chair, or else by employing a stand placed behind the sitter, and represented in the accompanying cut:—

Fig. 47.



The lower portion or foot of this stand consists of a heavy iron



casting, from which rises an adjusting rod, surmounted by two moveable pads, which are applied to the back of the head when in the required position, and fastened by proper screws.

The eyes should be directed to some definite object, which should be of a dark colour, and may be winked as often as required without injuring the portrait, provided the head is kept perfectly steady. A complete fixedness of look should be avoided, and the sitter should as much as possible divest himself of the idea that he is about to have his portrait taken, and rather assume his usual and easy appearance.

To give a finish to a portrait it is necessary to have some kind of background placed just behind the person; either a painted screen representing a view, or terrace, library, &c., can be used, or a plain background of some even colour, either of a dark or light shade according to the colour of the dress or complexion of the sitter. A black or drab will be found the best colour for dark, and a light brown for the light background. The best height for the camera is about level with the sitter's eyes.

*Views, &c.*—For views and buildings, the best guide for the operator is the picture as represented on the ground glass of the camera. But if any great portion of the picture appears more brightly illuminated than the rest, as a bright sky, or white building, ascertain in what position some opaque body or thick handkerchief can be held before the lens of the camera, so as to prevent so great a quantity of light reaching the glass from that particular object, and hold the handkerchief in the position that has been thus ascertained during some portion of the time the plate or paper is exposed in the camera, which will tend to equalise the action of the light, and thus produce a better picture.

Care should also be taken that the rays of the sun do not impinge on the lens of the camera, otherwise the picture obtained will be wanting in distinctness of detail.

*Engravings, &c.*—To produce these very beautiful photographs, the only hints necessary to be attended to are to place them in a good light, on a perfectly flat surface, which should be parallel with the lens of the camera, and they ought not to be covered with glass, which is apt by its reflection to injure the picture.

## ADDENDA.

### PREPARATION OF ALBUMINIZED PAPER FOR POSITIVE PICTURES.

As many operators have obtained very beautiful proofs with inferior paper from negatives, on both glass and paper, by the process described by M. De Gray, I give his details, as translated by Mr. Cousins:—

“Take white of eggs, to which add the fifth part, by volume, of saturated solution of chloride of sodium, or what is still better, hydrochlorate of ammonia; then beat it into a froth, and decant the clear liquid after it has settled for one night. Pour the solution into a dish, placed horizontally, taking care that there is no froth; then take the paper that you have chosen, and wet it on one side only, beginning at the edge of the dish which is nearest to you, and the largest side of the sheet, placing the right angle on the liquid, and inclining it towards you; advance it in such a manner as to exercise a pressure which will remove the air-bubbles and to push them out if they remain.

“Let the leaf imbibe for a minute at most, without touching it; then take it up gently, but at once, with a very regular movement, and hang it up by the corner to dry.

“You prepare thus as many leaves as you wish in the same bath, taking care that there is always about a quarter of an inch in depth of the solution in the dish; then place your sheets (thus prepared and dried) one on the other between two leaves of white paper, and pass over them several times a very hot iron, taking out a leaf each time; you will thus render the albumen insoluble.

“The iron should be as hot as it can be without scorching the paper.

“The paper thus prepared is very highly varnished. If you desire to obtain less gloss, add, before beating the eggs, the

half or more of distilled water, containing equally a fifth of water saturated with hydrochlorate ammonia. You may thus modify, at pleasure, the degree of brilliancy of the proof. The mixture of half albumen and half water is excellent; it gives much fineness and firmness, without giving the proof a varnished appearance little in-artistic.

“ You may keep this paper some time before you apply the nitrate of silver to it, as it does not spoil.

“ When you desire to use it, put the albumen side on a bath of nitrate of silver, containing one part of nitrate by weight to four of distilled water, and let it imbibe four or five minutes; then hang it by the corner to dry.

“ This paper gives much depth to the blacks, and great brilliancy to the whites. In leaving it a shorter time on the nitrate bath (about one minute), and using Whatman's paper, you may obtain a reddish purple tint, very harmonious. Canson's papers, and usually all those which contain much amidine, give black tints.

#### FIXING THE POSITIVE PROOF.

“ The positive proof when obtained is not permanent; you must fix it directly by the following operation:—Dissolve in a bottle hyposulphite of soda, three ounces; filtered water, about one pint. In another bottle dissolve about 70 grains of nitrate of silver in a glass or two of water; when well dissolved, you add to it saturated solution of chloride of sodium, until the white precipitate ceases to fall; allow it to repose a short time, and then decant the clear liquor, and gather the precipitate of chloride of silver, which you dissolve in the other bottle of hyposulphite; by this means you obtain directly the black tints with the hyposulphide thus prepared. The older the hyposulphite is, the better; when it gets thick, you must add a fresh solution of hyposulphite alone, without the chloride of silver, the old containing an excess, which it has taken from the proofs already immersed in it. You must not filter it to take away the deposit, but only let it repose in a large bottle, and decant the clear liquid for use, leaving the sediment to be re-dissolved by fresh hyposulphite.

“ By leaving the proofs a longer or shorter period in the bath, you

can obtain all the tints from the red to the black, and clear yellow; with a little practice you will be sure to get the tint you desire. You must not leave a proof less than an hour in the bath for it to be sufficiently fixed, and it can remain three or four days to obtain the sepia and yellow, by heating the hyposulphite. I accelerate the operation, but must not then leave the proof for an instant to itself, as the rapidity of action is so great that the picture might be completely effaced.

“By adding to the preceding hypo. solution 15 grammes (1.4th part) of liquid ammonia, I obtain pretty bister tints, and very pure whites; the English paper is exceedingly good for these tints.

“I obtain also fine velvet-like tints by putting it (when taken out of the hyposulphite of soda) upon a bath of salt of gold, using 15 grains of chloride of gold to one pint of distilled water.

“Fine yellow tints are obtained by placing the proof (if very vigorous) first in a bath of hyposulphite of soda and then in a bath composed of one pint of water and one fluid ounce of hydrochloric acid, washing it perfectly in water; liquid ammonia, employed in the same quantity as last mentioned, gives remarkably fine tints.

“When the proof is the colour you desire wash it in several waters, and leave it two or three hours in a basin of water, until, touching it with the tongue, you perceive no sweet taste which indicates the presence of hyposulphite of silver; then dry it by hanging it up, and it is finished. The bath of hyposulphite of soda may contain as many proofs as you please; but care must be taken to get rid of air bubbles between the sheets, which would otherwise produce indelible black stains. I use, to agitate the proofs, a long silk pencil, by the aid of which I get rid of the defects formed upon them. The taking positive proofs requires great care and attention, and must not be treated as a secondary operation. It is necessary to calculate the time by the subject and effect you wish to produce. When any peculiar effect is to be produced, put only one proof in the bath at a time.”

## PHOTOGRAPHS ON WAXED PAPER.

By modifying the process of M. De Gray, just described, by employing the albumised paper as the ordinary paper in the calotype process, very good negative pictures can be produced on very indifferent paper, due, no doubt, to the circumstance of the impression of the light being confined to the surface; many plans have been proposed to effect this purpose, besides the employment of albumen, such as lacturine, caseine, solution of gutta serena, &c., but no substance has been found to answer better than wax, which is employed most successfully in the following manner, as described by Mr. Hunt:—"A sheet of good writing paper is placed upon a hot iron plate, and rubbed over with wax until thoroughly saturated, taking care that the wax is uniformly diffused. If there should be an accumulation in any part, the paper is to be held up by one corner, in front of a fire sufficiently hot to liquefy it, and allow it to flow off from the opposite corner. A great many sheets of this paper can be prepared at a time, and kept until required. To give these the sensitive coating, a large dish must be procured, and filled with a solution of iodide of potassium, made by dissolving about 500 grains of the iodide in a pint of water; if the paper is simply dipped in and then removed, it will be found to remain quite dry, owing to the repulsive action exerted between the water and the wax. Sheets of waxed paper are to be passed into the solution one after another, taking care to remove any air bubbles which may form on the surface of each, until as many as may be required are inserted, and the whole allowed to remain two or three hours. In that time a considerable quantity of iodide of potassium has been absorbed, and, on removing the papers and drying them, it will be found, on the application of a solution of nitrate of silver (about 17 grs. to the ounce) that a beautiful surface of iodide is produced, and can be rendered sensitive when required by the ordinary calotype process, with "gallo-nitrate of silver," and the picture developed either with the gallo-nitrate of silver or solution of protosulphate of iron. The resulting pictures are beautifully transparent, not in any respect inferior for copying from than those negatives which are waxed after the picture has been obtained, and all the details are very charmingly preserved."

ON THE PRODUCTION OF INSTANTANEOUS PHOTOGRAPHIC IMAGES.

The circumstance of Mr. Fox Talbot having succeeded in obtaining a photographic picture of a printed paper fastened upon a wheel, which was revolved as rapidly as possible, and illuminated by a sudden electric discharge, has been known for some months past; but the method of preparing the sensitive surface has only just appeared in a communication from the discoverer, printed in the *Athenæum* of December 6, 1851, and from which the following details are taken:—

“ 1. Take the most liquid portion of the white of an egg, rejecting the rest. Mix it with an equal quantity of water. Spread it very evenly upon a plate of glass, and dry it at the fire. A strong heat may be used without injuring the plate. The film of dried albumen ought to be uniform and nearly invisible.

“ 2. To an aqueous solution of nitrate of silver add a considerable quantity of alcohol, so that an ounce of the mixture may contain three grains of the nitrate. I have tried various proportions, from one to six grains, but perhaps three grains answer best. More experiments are here required, since the results are much influenced by this part of the process.

“ 3. Dip the plate into this solution, and then let it dry spontaneously. Faint prismatic colours will then be seen upon the plate. It is important to remark, that the nitrate of silver appears to form a true chemical combination with the albumen, rendering it much harder, and insoluble in liquids which dissolved it previously.

“ 4. Wash with distilled water to remove any superfluous portions of the nitrate of silver. Then give the plate a second coating of albumen similar to the first; but in drying it avoid heating it too much, which would cause a commencement of decomposition of the silver. I have endeavoured to dispense with this operation No. 4, as it is not so easy to give a perfectly uniform coating of albumen as in No. 1. But the inferiority of the results obtained without it induces me for the present to consider it as necessary.

"5. To an aqueous solution of prot-iodide of iron add first an equal volume of acetic acid, and then 10 volumes of alcohol. Allow the mixture to repose two or three days. At the end of that time it will have changed colour, and the odour of acetic acid as well as that of alcohol will have disappeared, and the liquid will have acquired a peculiar but agreeable vinous odour. It is in this state that I prefer to employ it.

"6. Into the iodide thus prepared and modified the plate is dipped for a few seconds. All these operations may be performed by moderate daylight, avoiding however the direct solar rays.

"7. A solution is made of nitrate of silver, containing about 70 grains to one ounce of water. To three parts of this add two of acetic acid. Then if the prepared plate is rapidly dipped once or twice into this solution it acquires a very great degree of sensibility, and it ought then to be placed in the camera without much delay.

"8. The plate is withdrawn from the camera, and in order to bring out the image it is dipped into a solution of protosulphite of iron, containing one part of the saturated solution diluted with two or three parts of water. The image appears very rapidly.

"9. Having washed the plate with water it is now placed in a solution of hyposulphite of soda; which in about a minute causes the image to brighten up exceedingly, by removing a kind of veil which previously covered it.

"The plate is then washed with distilled water, and the process is terminated. In order, however, to guard against future accidents, it is well to give the picture another coating of albumen or of varnish."

Mr. Fox Talbot states that success will greatly depend upon the iodide of iron which is employed, being "in a peculiar or definite chemical state;" and "that in the last washing, No. 10, the image maybe rubbed strongly with cotton and water without any injury to it; but, on the contrary, with much improvement, as this removes any particles of dust or other impurity, and gives the whole picture a fresh degree of vivacity and lustre."

"5. To an aqueous solution of protiodide of iron add first an equal volume of acetic acid, and then 10 volumes of alcohol. Allow the mixture to repose two or three days. At the end of that time it will have changed colour, and the colour of acetic acid as well as that of alcohol will have disappeared, and the liquid will have acquired a peculiar but agreeable vinous odour. It is in this state that I prefer to employ it."

"6. Take the iodide thus prepared and modified the plate is dipped for a few seconds. All these operations may be performed by moderate daylight, avoiding however the direct solar rays."

"7. A solution is made of nitrate of silver, containing about 70 grains to one ounce of water. To three parts of this add two of acetic acid. Then if the prepared plate is rapidly dipped once or twice into this solution it acquires a very great degree of sensibility, and it ought then to be placed in the camera without much delay."

"8. The plate is withdrawn from the camera, and in order to bring out the image it is dipped into a solution of protochloride of iron, containing one part of the saturated solution diluted with two or three parts of water. The image appears very readily."

"9. Having washed the plate with water it is now placed in a solution of hyposulphite of soda; which in about a minute causes the image to brighten up exceedingly, by removing a kind of veil which previously covered it."

"The plate is then washed with distilled water, and the process is continued. In order, however, to guard against future defects, it is well to give the picture another coating of albumen or of varnish."

Mr. Fox Talbot states that success will greatly depend upon the mode of ton which is employed, being "a peculiar or definite chemical state;" and "that in the best washing, No. 10, the tinge may be rubbed strongly with cotton and water without any injury to it; but on the contrary, with much improvement, as this removes a portion of dust or other impurity, and gives the whole picture a fresh degree of vivacity and lustre."



# INDEX.

	PAGE		PAGE
Acetic acid .....	28	Gallo nitrate of silver .....	43
Achromatic lenses .....	20	Gold, solution of .....	58
Actinism .....	13	Head rest .....	66
Albumen pictures .....	64	Hungarian solution .....	55
Albumenized paper .....	68	Hyposulphite of soda .....	29
Ammoniacal nitrate of silver.	33	Instantaneous process .....	72
Anthotype .....	31	Iodine .....	27
Bromide of iodine .....	55	Iodide of potassium .....	27
Bromide of lime.....	55	Iodide of silver .....	41
Bromide of potassium .....	28	Iodized paper.....	40
Bromine .....	27	Iodized paper, how used ...	43
Bromine apparatus .....	54	Iodizing apparatus .....	53
Buckle's brush .....	35	Lampblack, preparation of ..	49
Bufs, construction of .....	50	Lenses, kinds of .....	6
Calotype process .....	39	Levelling stand.. ..	50
Calotype pictures, how deve-		Mercury box .....	57
loped .....	44	Nitrate of silver .....	27
Calotype pictures, how fixed	45	Paper, how iodized .....	40
Calotype pictures, how copied	47	Paper, selection of .....	32
Cameras, photographic.....	16	Photogenic drawing .....	30
Cameras, portable folding ...	22	Photogenic drawing, how fixed	37
Cameras, stands for .....	24	Photogenic paper, prepara-	
Chloride of bromine .....	54	tion of .....	33
Collodion pictures .....	61	Photographs, negative and	
Collodion, preparation of ....	64	positive .....	38
Colouring daguerreotypes ..	59	Photographs on waxed paper	71
Crysoyte .....	31	Photography on glass .....	61
Cundell's camera.....	18	Plate box .....	52
Cyanotype.....	31	Plate holder .....	51
Daguerreotype .....	47	Pyrogallic acid.....	29
Daguerreotype plates .....	48	Polishing bufs .....	50 and 52
Daguerreotype plates, how		Refraction .....	3
polished .....	49	Rouge, how prepared .....	49
Distillaion, how performed .	26	Reversing frame .....	36
Electro-silvering plates ....	60	Solar spectrum.....	14
Energia .....	14	Spherical aberration.....	7
Filtering, how performed ..	25	Talbotype .....	39
Focus, meaning of .....	10	Tripoli, preparation of .....	49
Gallic acid .....	28	Woolcott's accelerator .....	55

# INDEX.

<p>Woolcott's accelerator . . . . . 55</p> <p>Tribol, preparation of . . . . . 49</p> <p>Talotype . . . . . 59</p> <p>Spherical aberration . . . . . 7</p> <p>Solar spectrum . . . . . 14</p> <p>Reversing frame . . . . . 38</p> <p>Range, how prepared . . . . . 49</p> <p>Reflection . . . . . 3</p> <p>Polishing balls . . . . . 59 and 63</p> <p>Pyroelectric card . . . . . 29</p> <p>Plate holder . . . . . 51</p> <p>Plate box . . . . . 63</p> <p>Photography on glass . . . . . 61</p> <p>Photographs on waxed paper . . . . . 71</p> <p>Positive . . . . . 38</p> <p>Photographic negative and              tion of . . . . . 38</p> <p>Photogenic paper, prepara-              tion of . . . . . 37</p> <p>Photogenic drawing, how fixed . . . . . 37</p> <p>Photogenic drawing . . . . . 39</p> <p>Paper, selection of . . . . . 62</p> <p>Paper, how oxidized . . . . . 49</p> <p>Plate of silver . . . . . 27</p> <p>Mercury box . . . . . 67</p> <p>Leveling stand . . . . . 6</p> <p>Lenses, kinds of . . . . . 6</p> <p>Lampblack, preparation of . . . . . 49</p> <p>Locking apparatus . . . . . 63</p> <p>Loxided paper, how used . . . . . 43</p> <p>Loxided paper . . . . . 49</p> <p>Iodide of silver . . . . . 41</p> <p>Iodide of potassium . . . . . 27</p> <p>Iodine . . . . . 27</p> <p>Instantaneous process . . . . . 72</p> <p>Hypocyanite of soda . . . . . 29</p> <p>Hungarian solution . . . . . 53</p> <p>Head rest . . . . . 68</p> <p>Gold solution of . . . . . 55</p> <p>Gallo nitrate of silver . . . . . 43</p>	<p>Yellie acid . . . . . 28</p> <p>Zeiss's camera . . . . . 18</p> <p>Grays . . . . . 31</p> <p>Obtaining daguerotypes . . . . . 43</p> <p>Collodion, preparation of . . . . . 61</p> <p>Collodion pictures . . . . . 61</p> <p>Chloride of bromine . . . . . 64</p> <p>Camera stands for . . . . . 64</p> <p>Camera, portable taking . . . . . 32</p> <p>Lenses, portable taking . . . . . 32</p> <p>Lambs, photogenic . . . . . 18</p> <p>Calotype pictures, how cupped . . . . . 47</p> <p>Calotype pictures, how fixed . . . . . 44</p> <p>Calotype pictures, how devel-              oped . . . . . 44</p> <p>Calotype process . . . . . 39</p> <p>But, construction of . . . . . 50</p> <p>Buckle's dish . . . . . 62</p> <p>Bromine apparatus . . . . . 64</p> <p>Bromine . . . . . 27</p> <p>Bromide of potassium . . . . . 28</p> <p>Bromide of lime . . . . . 55</p> <p>Bromide of iodine . . . . . 65</p> <p>Anhydrate . . . . . 21</p> <p>Ammoniacal nitrate of silver . . . . . 28</p> <p>Albumenized paper . . . . . 65</p> <p>Albumen pictures . . . . . 64</p> <p>Actinon . . . . . 16</p> <p>Achromatic lenses . . . . . 28</p> <p>Acetic acid . . . . . 28</p>
--	--